A STUDY OF THE TEMPERATURE GRADIENTS OF GASES FLOWING THROUGH HEATED POROUS METAL

by

Lt. Cdr. D. J. O'Meara, U.S.N.
Lt. Cdr. C. C. Andrews, U.S.N.

Thesis
055

DUDLEY KNOX LIBRARY
NAVAL POSTGRADUATE SCHOOL
MONTEREY CA 93943-5101

A STUDY OF THE [illegible]
OF [illegible] FIELD [illegible]
[illegible]

Thesis by

Lt. Cdr. D. J. O'Meara, U.S.N.

and

Lt. Cdr. C. C. Andrews, U.S.N.

In partial fulfillment of the requirements
for the degree of Aeronautical Engineer

California Institute of Technology
Pasadena, California

1947

Thesis
055

DUDLEY KNOX LIBRARY
NAVAL POSTGRADUATE SCHOOL
MONTEREY CA 93943-5101

Part	Title	Page
	Summary	
I	Introduction	1
II	Description of Apparatus and Test Procedure	2
III	Discussion	3
IV	Results Tabulated	8
V	Results Plotted	19
VI	Conclusions	42
VII	Diagrams and Photographs	
	(A) Schematic Diagram of Apparatus	43
	(B) Detail Drawings of Porous Metal Pack	44
	(C) Photographs of Apparatus	45
VIII	Sample Calculations	
	(A) Summary of Mass Flow Calculations	46
	(B) Summary of Heat Transfer Calculations	49
IX	Appendix	50
	Discussion of Efforts to Accomplish Uniform Heating of a Specimen by Electrical Resistance Heating	

8083

ACKNOWLEDGMENT

The authors wish to express their gratitude to Dr. Pol Duwez and to Mr. H. L. Wheeler of the CALCIT Jet Propulsion Laboratory. Dr. Duwez's helpful criticism and interpretation of the data have contributed immeasurably in the preparation of this report. Mr. Wheeler interested them in the problem studied and gave invaluable guidance in the design and preparation of the equipment employed.

SUMMARY

Nitrogen and Hydrogen were passed through a pack of heated porous metal discs to obtain temperature distribution as a function of (1) mass flows and (2) temperatures at which metal was heated. An effort was made to obtain heat transfer per unit volume of porous metal as a function of (1) mass flows and (2) temperatures at which the metal was heated. By varying inlet gas pressures at various metal temperatures the effect of temperature on pressure drop was determined.

The results show that a cool gas flowing through a heated porous metal very quickly assumes the temperature of the metal. Heat transfer appears to increase linearly with mass flow up to a certain point above which the results were inconclusive. The variation of mass flow with pressure drop was determined to be linear for low pressure drop and to increase at a greater rate for higher pressure drops.

INTRODUCTION

This study was prompted by the desire to learn the effects of passing a cold gas through a uniformly heated porous metal, namely, the temperature distribution of the gas as a function of mass flow and as a function of the difference between the incoming gas temperature and various temperatures at which the metal was heated. In the investigation, however, it was realized that since the source of heat was external it was necessary that heat flow from the perimeter of the specimens radially inward which caused a temperature variation across the diameter of the specimens. This variation produced an effect in the measured results.

The investigation as carried out was very preliminary in nature due to the limitations of the equipment. It is believed, however, that this investigation provided both useful information and a stepping off place for further investigation of this important problem.

DESCRIPTION OF [illegible] PROCEDURE.

The following listed items of equipment comprised the apparatus:

No.	Item
10	40% porous stainless steel sintered discs of 3/4" diameter and 1/10" thickness.
10	Brass rings, 3/10" thickness, 3/4" inner diameter, and 2" outer diameter.
30	Garglock gaskets cut to same diameters as brass rings.
13	Iron-constantan thermocouples with glass insulation lead wires.
1	Stainless steel tube, 2-1/2" diameter, 8" in length.
1	Steel tube, outer diameter 2-1/4", inner diameter 1-3/4", length 11".
1	Steel tube, outer diameter 2-1/4", inner diameter 1-3/4", length 20".
1	3/8" standard black pipe 16-1/2" long.
1	3/8" standard black pipe 30" long.
1	Pressure regulator.
1	Pressure gage.
1	Furnace, 3.4 K.W., combustion tube type.
1	Flow meter, volumetric type.
1	Micromax complete with thermocouple.
1	Selector switch, 11 pt.
1	Potentiometer, Leeds and Northrup.
2	Steel discs, 3/8" thickness, outer diameter 2", inner diameter tapped for 3/8" pipe threads.
4	Barrier strips, 8 pt.

DESCRIPTION OF [illegible] RUNS

The apparatus consisted of the above listed equipment so assembled to permit the flow of nitrogen and hydrogen gases through a pack of heated porous metal specimens and the recording of the required data. The brass rings (item No. 5, Fig. 25) were shrunk over the metal specimens (item No. 7, Fig. 25) to effect firm mountings for the specimens, to insure a ready heat flow to the specimens and to prevent a gas leakage between the rings and specimens. Eleven thermocouples were mounted in the garlock gaskets by spreading the gasket material apart and inserting the thermocouples radially through the opening (Fig. 29). This was found to be necessary in order to insure the correct positioning of the thermocouple beads and to prevent the thermocouple beads from causing a gas leakage. The rings were placed face to face with three gaskets on each side of each ring (one gasket on either side of the center gasket holding the thermocouple) (Fig. 29). A thermocouple was mounted in each of two metal specimens (the first and second specimens from the gas inlet end) (Figs. 25 and 29). All thermocouple leads were placed in a groove cut longitudinally along the outer side of the cylindrical pack and lead out on the gas outlet end (Fig. 23). The pack was then inserted in the stainless steel tube (item No. 4, Figure 25). Steel discs (item No. 3, Fig. 25) (of same diameter as brass rings) into which the 3/8" black pipes were threaded were then inserted at either end of the tube. The threaded steel tubes (items Nos. 1 and 10, Fig. 25) were then tightly

screwed into either end of the [illegible] steel tube, their ends butting against the outer faces of the steel discs. Sufficient compression of the brass rings was accomplished in this design to prevent gas leakage to at least 100 psi gas pressure. This unit made up of the three sections of tubing was then placed in the furnace as shown by photographs.

The gas was introduced into the apparatus from a standard 2500 psi bottle, through a pressure regulator valve and a cooling coil (Fig. 24). Recorded pressures of the incoming gas were read from a sensitive gage mounted at the end of the 3/8" pipe leading into the pack. The gas discharged from the pack through the 3/8" pipe mounted on the outgoing end of the pack into another cooling coil, and from there to the flow meter.

The thermocouple leads were lead through the clearance between the steel tube and the 3/8" pipe on the outgoing end to barrier strips mounted on the outer end of the 3/8" pipe. Leads from the eleven point selector switch were connected to the barrier strips and to the potentiometer permitting the ready sampling of gas and metal temperatures.

The furnace temperature was controlled by a micromax. The thermocouple indicating the furnace temperature to the micromax was inserted between the outgoing steel tube and the outgoing 3/8" pipe, and butted against the steel disc which was located approximately in the center of the furnace. Furnace temperatures recorded in results were indicated by this thermocouple.

Procedure

All data recorded were under conditions of equilibrium. The procedure, therefore, was to heat the pack in the furnace to the desired temperature while the gas was flowing at the desired rate and adjust the power input to the furnace (by a rheostat control) to maintain equilibrium conditions. Because of the long time required to change the temperature of the pack in the furnace all flow rates for the gas were taken at one furnace temperature before changing the furnace temperatures.

Because of the variable flow of heat from the pack along the entry pipe it was impractical to keep the gas inlet temperature constant for all furnace temperatures and rates of flow. Means of cooling by immersing the inlet cooling coils in CO_2 ice and blowing cold gas over the entry pipe were employed. These methods, however, proved inadequate with the apparatus used.

The heated gas discharged from the pack was cooled in a coil immersed in a container of water. Cooling was necessary due to temperature restrictions on the gas flow meter. The temperature of the gas entering the flow meter was the same as that of the cooling water.

DISCUSSION

In an effort to compare gas and metal temperatures a thermocouple was imbedded in each of the first two specimens from the inlet end of the pack. Temperatures indicated by these thermocouples were found to differ a small amount from the temperatures indicated by the thermocouples in the gas stream emerging from the specimens. These temperature differences were not determined precisely, but it was concluded that the gas temperature was of the order of from one to ten degrees lower than the metal temperature, depending, of course, on the rate of mass flow.

By varying the mass flow at constant furnace temperatures, relative temperature distributions were determined (Figs. 1 to 6). At low mass flows the temperatures of the gases were found to increase rapidly in the first few specimens and then increase at a slower and slower rate as the gas temperature approached that of the furnace. At higher mass flows the gas temperatures were found to approach the furnace temperatures at a more nearly linear rate. Final gas temperatures were higher for lower mass flows.

Two gases, nitrogen and hydrogen, were flowed through the heated porous metal pack to obtain comparative data on mass flow, temperature distribution, and heat transfer, for constant pressure drops and constant furnace temperatures. It was found that mass flows were approximately proportional to the molecular weights of the two gases. Temperature distributions for the two gases were found to be similar. Due to the limitations of the apparatus used the heat transfer data obtained were not adequate to make conclusive comparisons.

The external heating resulted in temperature variations diametrically across the specimens. Since the gas temperatures were taken at the center of the stream they were lower than average gas temperatures over a cross-section. This effect gave temperature gradient curves with less slope than would have been obtained with more nearly uniform heating.

An effort was made to determine the variation of heat transfer with mass flow at constant furnace temperatures. Heat transfer appeared to increase linearly with mass flow up to a certain point above which the results were not conclusive (Figs. 22 and 23).

Furnace Temperature = 70°F

Nitrogen Gas

Gas Inlet Pressure (psi)	Flow Rate (sec/1.0 ft^3)	Mass Flow (lb/in^2-sec) x 10^{-4}
10	313.2	4.9
20	159.3	9.64
30	104.8	14.66
40	75.9	20.2
50	57.8	26.6
60	47.2	32.5

Furnace Temperature = 400 °F

Nitrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	2.50	118	4.47	185	4.05	170	2.99	135
2	6.61	256	7.36	280	6.95	268	5.06	205
3	7.98	301	8.61	322	8.42	315	6.27	245
4	9.03	335	9.20	344	9.43	348	7.25	277
5	9.71	357	9.30	360	10.08	380	7.82	296
6	10.10	370	10.15	371	10.50	383	8.30	311
7	10.38	379	10.40	380	10.83	395	8.76	328
8								
9	10.92	397	11.02	400	11.48	415	9.66	355
10								
0	11.39	412	11.56	417	11.91	430	10.46	382
1m	6.88	265	7.44	283	7.09	272	4.95	201
2m	5.41	216	6.80	262	6.60	255	5.00	203

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (sec/0.1 ft^3)	49.8	23	17	11.55
Furnace Temp. (°F)	410	430	420	400
Gas Outlet Temp. (°C)	25	23.5	17	20.5
Mass Flow (lb/in^2-sec) x 10^{-4}	3.28	6.27	9.8	14.3

Furnace Temperature = 600 °F

Nitrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	4.80	282	3.25	211	4.36	263	4.21	178	3.55	194
2	9.77	230	9.7	357	[illegible]	330	7.50	337	6.17	241
3	12.19	438	11.73	425	10.73	393	9.[illegible]	350	7.09	301
4	13.7	482	13.13	469	12.3	442	11.3	410	9.4[illegible]	347
5	14.7	520	14.17	502	13.36	476	12.1	435	10.4	380
6	15.23	537	14.73	522.4	14.16	502	12.97	404	11.31	410
7	15.5	546	15.17	535	14.61	517	13.54	482	12.0	432
8										
9	16.4	575	15.13	568	15.64	550	14.73	521	13.4	477.5
10			16.5	579	15.95	560	15.32	540	14.15	503
0	16.65	583	16.83	590	16.35	574	15.91	559	14.73	523
1m	10.2	373	10.12	370	8.83	320	7.52	295	6.74	247
2m	7.35	280								

Gas Inlet Pressure (psi)	5	10	20	30	40
Flow Rate (sec/0.1 ft^3)	111.6	60.1	32.5	19.5	13.1
Furnace Temp. (°F)	590	600	596	600	590
Gas Outlet Temp. (°C)	15	15.8	16.4	17.2	18.1
Mass Flow (lb/in^2-sec) x 10^{-4}	1.5	2.42	5.14	8.55	12.0[illegible]

Furnace Temperature = 800°F

Nitrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	6.09	256	4.36	181	4.42	183	4.55	191
2	13.28	474	11.18	400	9.66	355	8.30	321
3	16.3	572	14.3	507	12.9	458	11.57	413
4	18.3	637	16.7	585	15.13	534	13.3	464
5	19.5	676	18.3	637	16.9	588	15.08	532
6	21.15	697	19.25	668	18.1	650	16.4	575
7	20.5	709	19.9	690	19.9	680	17.5	611
8								
9	21.9	755	21.4	733	20.75	717	19.5	677
10	23.4	770	22.1	760	21.6	745	20.5	709
0	23.0	790	22.3	734	22.5	774	21.3	745
1m	13.7	437	11.68	422	10.1	370	8.71	325
2m								

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (Sec/0.1 ft^2)	84.5	40.8	24.1	16.1
Furnace Temp. (°F)	810	800	810	800
Gas Outlet Temp. (°C)	20.6	21.3	21.8	22.3
Mass Flow (lb/in^2-sec) x 10^{-4}	1.95	4.02	6.8	10.2

Furnace Temperature = 1000°F

Nitrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	12.09	435	9.11	333	9.03	335	8.09	305	7.04	270
2	19.0	660	16.3	572	15.0	530	13.91	494	12.53	450
3	22.0	760	20.2	700	18.3	637	16.7	585	15.75	555
4	24.2	830	22.2	750	21.1	720	19.5	676	18.5	644
5	25.5	870	24.2	820	23.3	784	21.4	738	20.3	702
6	26.3	896	25.3	865	24.1	825	22.9	787	22.0	767.5
7	26.8	912.5	26.1	890	25.1	858	23.95	820	25.3	800
8										
9	28.0	951	27.5	935	26.9	915	26.05	887	25.55	872
10	28.6	970	28.3	980	27.7	941	26.9	915	26.3	900
0	29.2	989	28.9	980	28.5	967	27.9	945	27.5	935
1m	19.9	690	17.3	605	16.0	562	14.21	504	13.79	488

Gas Inlet Pressure (psi)	10	20	30	40	50
Flow Rate (sec/0.1 ft^3)	115.4	56.3	34.8	22.3	16.1
Furnace Temp. (°F)	1000°	1000	1000	1000	1000
Gas Outlet Temp. (°C)	23	23	23	23	23
Mass Flow (lb/in^2-sec) x 10^{-4}	1.412	2.88	4.89	7.22	10.13

Furnace Temperature = 70°F

Hydrogen Gas

Gas Inlet Pressure (psi)	Flow Rate (sec/1.0 ft^3)	Mass Flow (lb/in^2-sec) x 10^{-6}
10	137	3.00
20	63.2	10.2
30	43.4	20.4
40	31	30.6
50	25.9	40.2
60	19.9	50.8

Furnace Temperature = 400°F

Hydrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	3.70	160	2.73	126	1.62	88	1.1	70
2	6.2	245	5.27	212	4.08	172	3.40	151
3	7.12	275	5.89	232	4.91	200	4.59	189
4	8.1	305	6.58	255	5.38	225	4.77	195
5	8.68	324	7.03	270	6.09	253	5.1	206
6	9.14	330	7.5	285	6.54	253	5.4	210
7	9.47	350	7.91	298	6.86	264	5.68	231
8								
9	10.24	375	8.88	330	7.91	298	6.96	262
10	10.53	386	9.3	345	8.41	315	7.45	284
0	10.8	393	9.63	355	8.91	331	7.85	297
1M	6.53	254	5.16	209	3.85	104	3.0	135
2M								

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (cc/1.0 ft^3)	261.7	120	70	47
Furnace Temp. (°F)	390	390	400	410
Gas Outlet Temp. (°C)	19	19	19	20
Mass Flow (lb/in^2-sec) x 10^{-5}	4.55	9.91	17.0	25.2

Furnace Temperature = 600

Hydrogen Gas

Thermocouple	Milli-volt	°F	Milli-volt	°F	Milli-volt	°F	Milli-volt	°F
1	5.97	235	3.34	148	1.81	95	1.1	70
2	10.28	376	8.57	320	6.06	238	4.13	173
3	11.73	418	10.02	367	7.45	283	5.62	223
4	13.2	471	11.68	423	9.1	337	6.89	268
5	14.03	499	12.73	455	10.11	370	7.48	283
6	14.6	517	13.34	485	11.03	402	8.2	303
7	15.1	533	14.3	507	12.01	432	9.12	338
8								
9	16.16	568	15.38	552	13.73	490	11.1	403
10	16.5	579	16.3	572	14.52	514	12.03	434
0	16.9	592	16.9	592	15.11	533	12.7	455
1m	10.62	392	8.81	321	5.92	234	3.95	167

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (sec/1 ft^3)	360	175	100	60
Furnace Temp. (°F)	600	610	600	585
Gas Outlet Temp. (°C)	22	23	23	23
Mass Flow (lb/in^2-sec) x 10^{-5}	3.27	6.93	11.76	19.55

8088

Furnace Temperature = 800°F

Hydrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	10.69	389	8.7	225	5.13	140	1.89	98
2	15.79	555	12.46	447	10.23	375	7.07	270
3	17.5	611	15.47	545	12.11	435	9.71	357
4	19.2	666	17.2	602	14.8	517	11.8	393
5	20.10	692	18.5	645	16.1	565	13.19	470
6	20.6	712	19.3	670	17.5	610	14.49	513
7	21.1	728	19.95	690	18.5	645	15.75	555
8								
9	22.25	765	21.5	741	20.5	709	18.45	642
10	22.8	784	22.1	760	21.3	735	19.55	678
0	23.2	796	22.65	778	21.9	755	20.4	705
1	16.3	572	13.8	475	10.11	370	7.2	275
2								

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (sec/1.0 ft^3)	462	224	125	77
Furnace Temp. (°F)	820	820	820	810
Gas Outlet Temp. (°C)	24	24	24.5	24.5
Mass Flow (lb/in^2-sec) x 10^{-5}	2.83	5.55	9.46	15.16

Furnace Temperature = 1000

Hydrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	13.4	477.5	9.12	339	5.11	206	2.9	132
2	18.7	650	19.4	673	15.45	545	10.05	365
3	20.8	719	21.8	750	18.5	645	14.63	510
4	22.1	760	23.7	813	21.2	731	17.3	607
5	23.1	794	24.6	841	22.7	780	18.9	657
6	23.7	813	25.3	865	23.0	820	20.4	705
7	24.3	832	25.9	884	24.0	849	21.7	748
8								
9	26.25	895	27.2	925	26.3	900	24.2	820
10	27.1	921	27.35	945	27.2	925	25.25	863
0	27.9	940	28.4	694	27.95	950	26.2	893
1n	19.3	670	19.7	683	15.58	549	11.14	405

Gas Inlet Pressure (psi)	10	20	30	40
Flow Rate (sec/1 ft^3)	484.6	284	158	91.3
Furnace Temp. (°F)	1010	1000	1000	990
Gas Outlet Temp. (°C)	26	25	25	25
Mass Flow (lb/in^2-sec) . 10^{-5}	2.36	4.42	7.59	12.72

Furnace Temperature = 1000°F

Hydrogen Gas

Thermocouple	Milli-volts	°F	Milli-volts	°F	Milli-volts	°F
1	1.80	97.5	1.72	94	1.67	90
2	6.34	247	5.49	219	4.30	181
3	11.34	410	11.61	420	7.02	285
4	12.52	449	12.55	450	7.4	282
5	14.07	500	14.05	500	8.14	306
6	15.45	545	15.47	545	8.87	330
7	16.85	590	17.0	595	9.84	361
8						
9	19.9	690	20.15	697	13.52	481
10	21.5	741	21.3	745	14.32	507
0	22.60	779	22.75	782	19.35	671
11	6.52	262	6.56	265	4.03	170
2						

Gas Inlet Pressure (psi)	50	60	70
Flow Rate (sec/1.0 ft^3)	57	45	27
Furnace Temp. (°F)	985	1000	980
Gas Outlet Temp. (°C)	25.5	26.5	27.5
Mass Flow (lbs/in^2-sec) x 10^{-5}	20.4	25.3	42.9

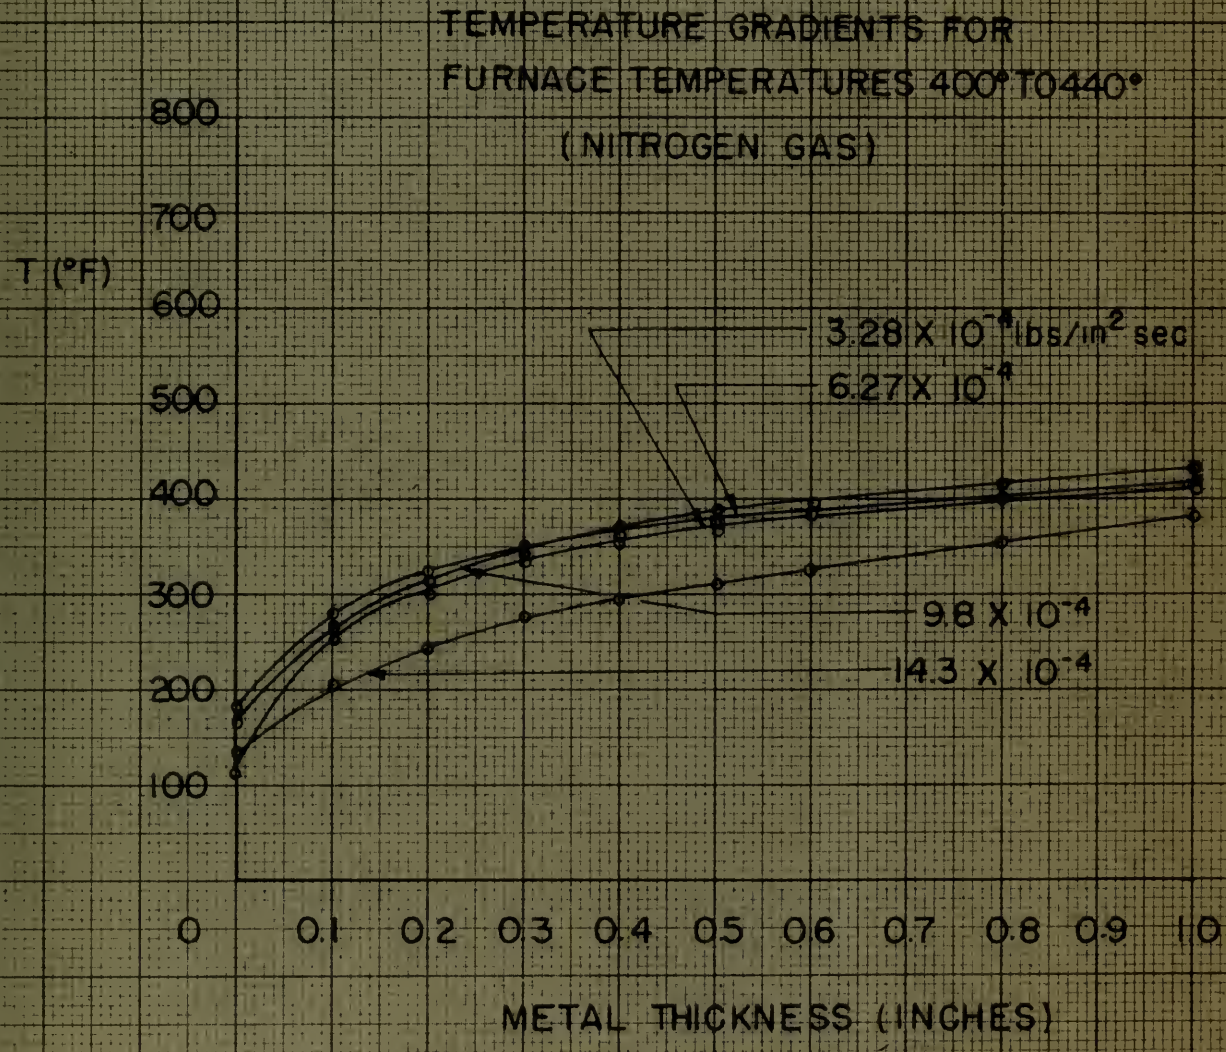
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURES 400° TO 440°
(NITROGEN GAS)
T (°F)
800
700
600
500
400
300
200
100
3.28 X 10⁻⁴ lbs/in² sec
6.27 X 10⁻⁴
9.8 X 10⁻⁴
14.3 X 10⁻⁴
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 1

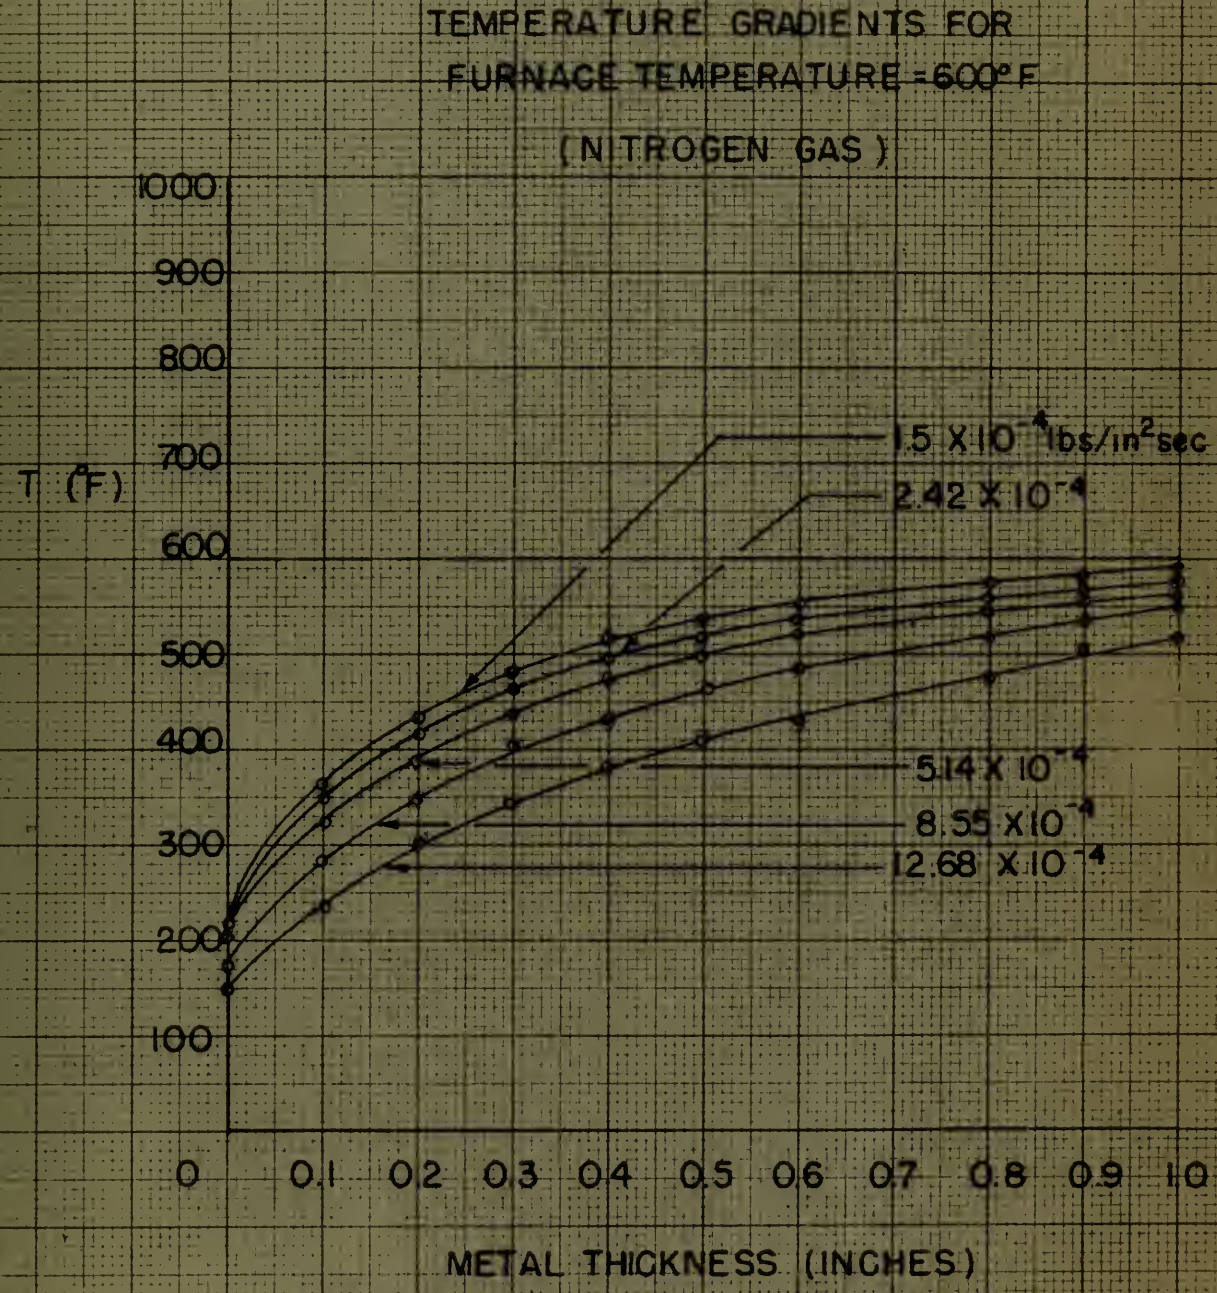
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 600° F
(NITROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
1.5 X 10⁻⁴ lbs/in² sec
2.42 X 10⁻⁴
5.14 X 10⁻⁴
8.55 X 10⁻⁴
12.68 X 10⁻⁴
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 2

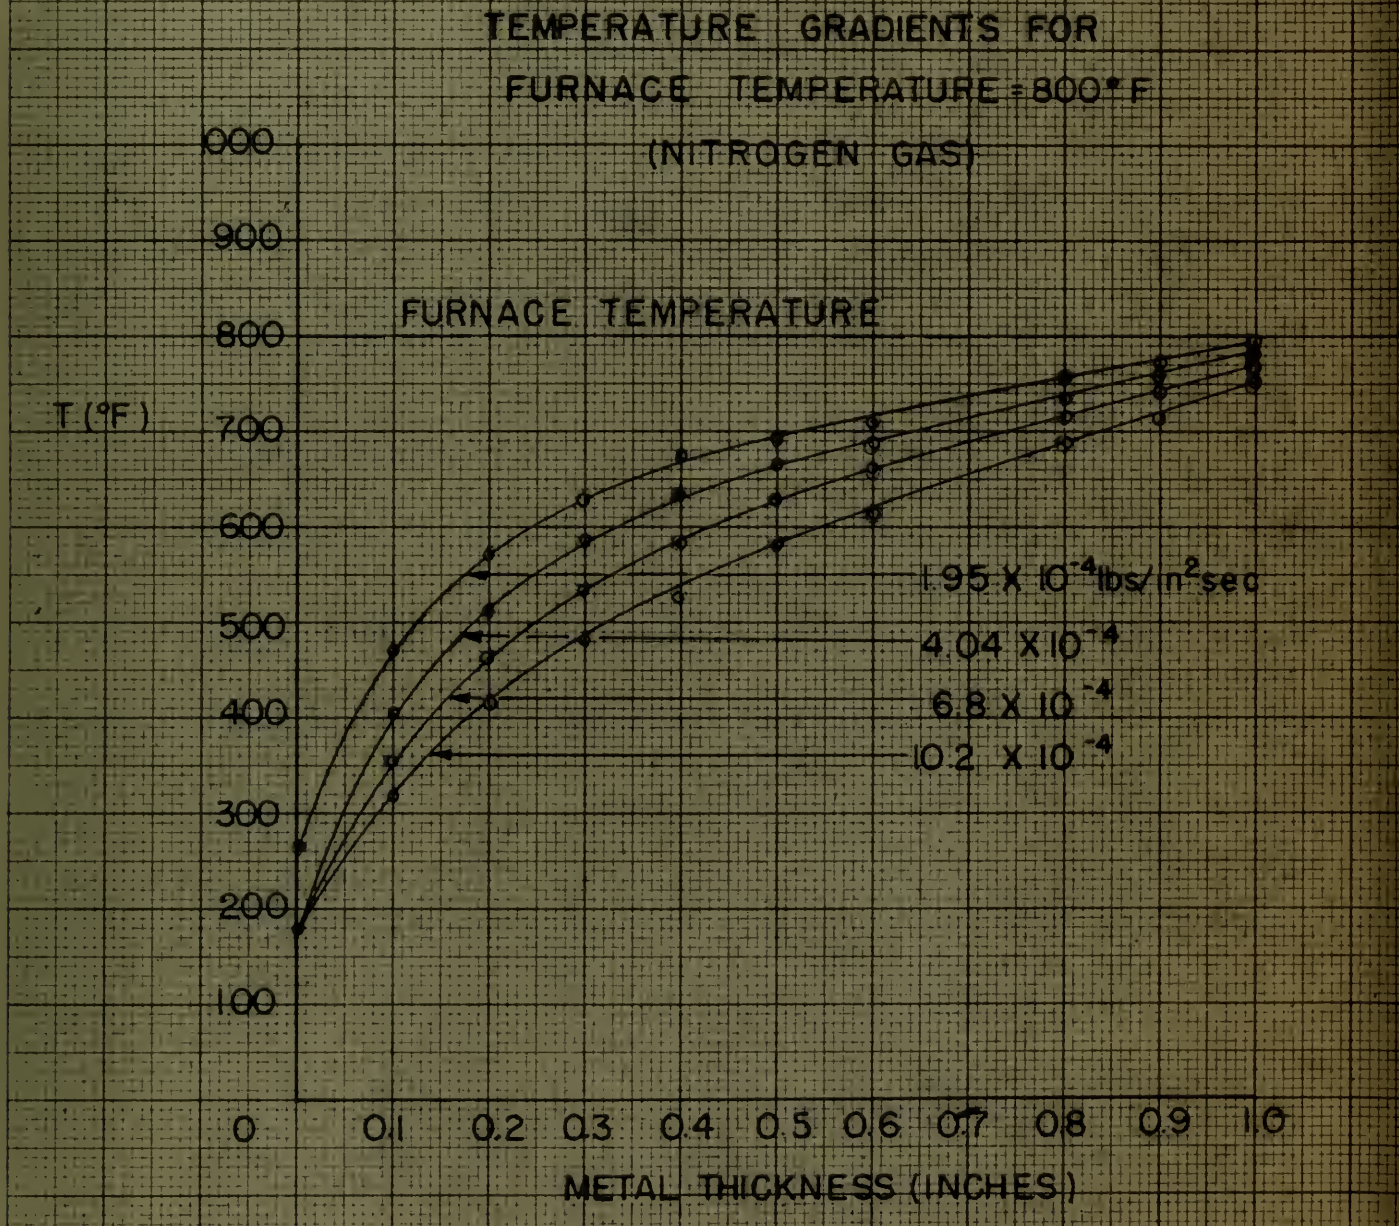
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 800° F
(NITROGEN GAS)
FURNACE TEMPERATURE
T (°F)
1000
900
800
700
600
500
400
300
200
100
1.95 X 10⁻⁴ lbs/in²sec
4.04 X 10⁻⁴
6.8 X 10⁻⁴
10.2 X 10⁻⁴
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 3

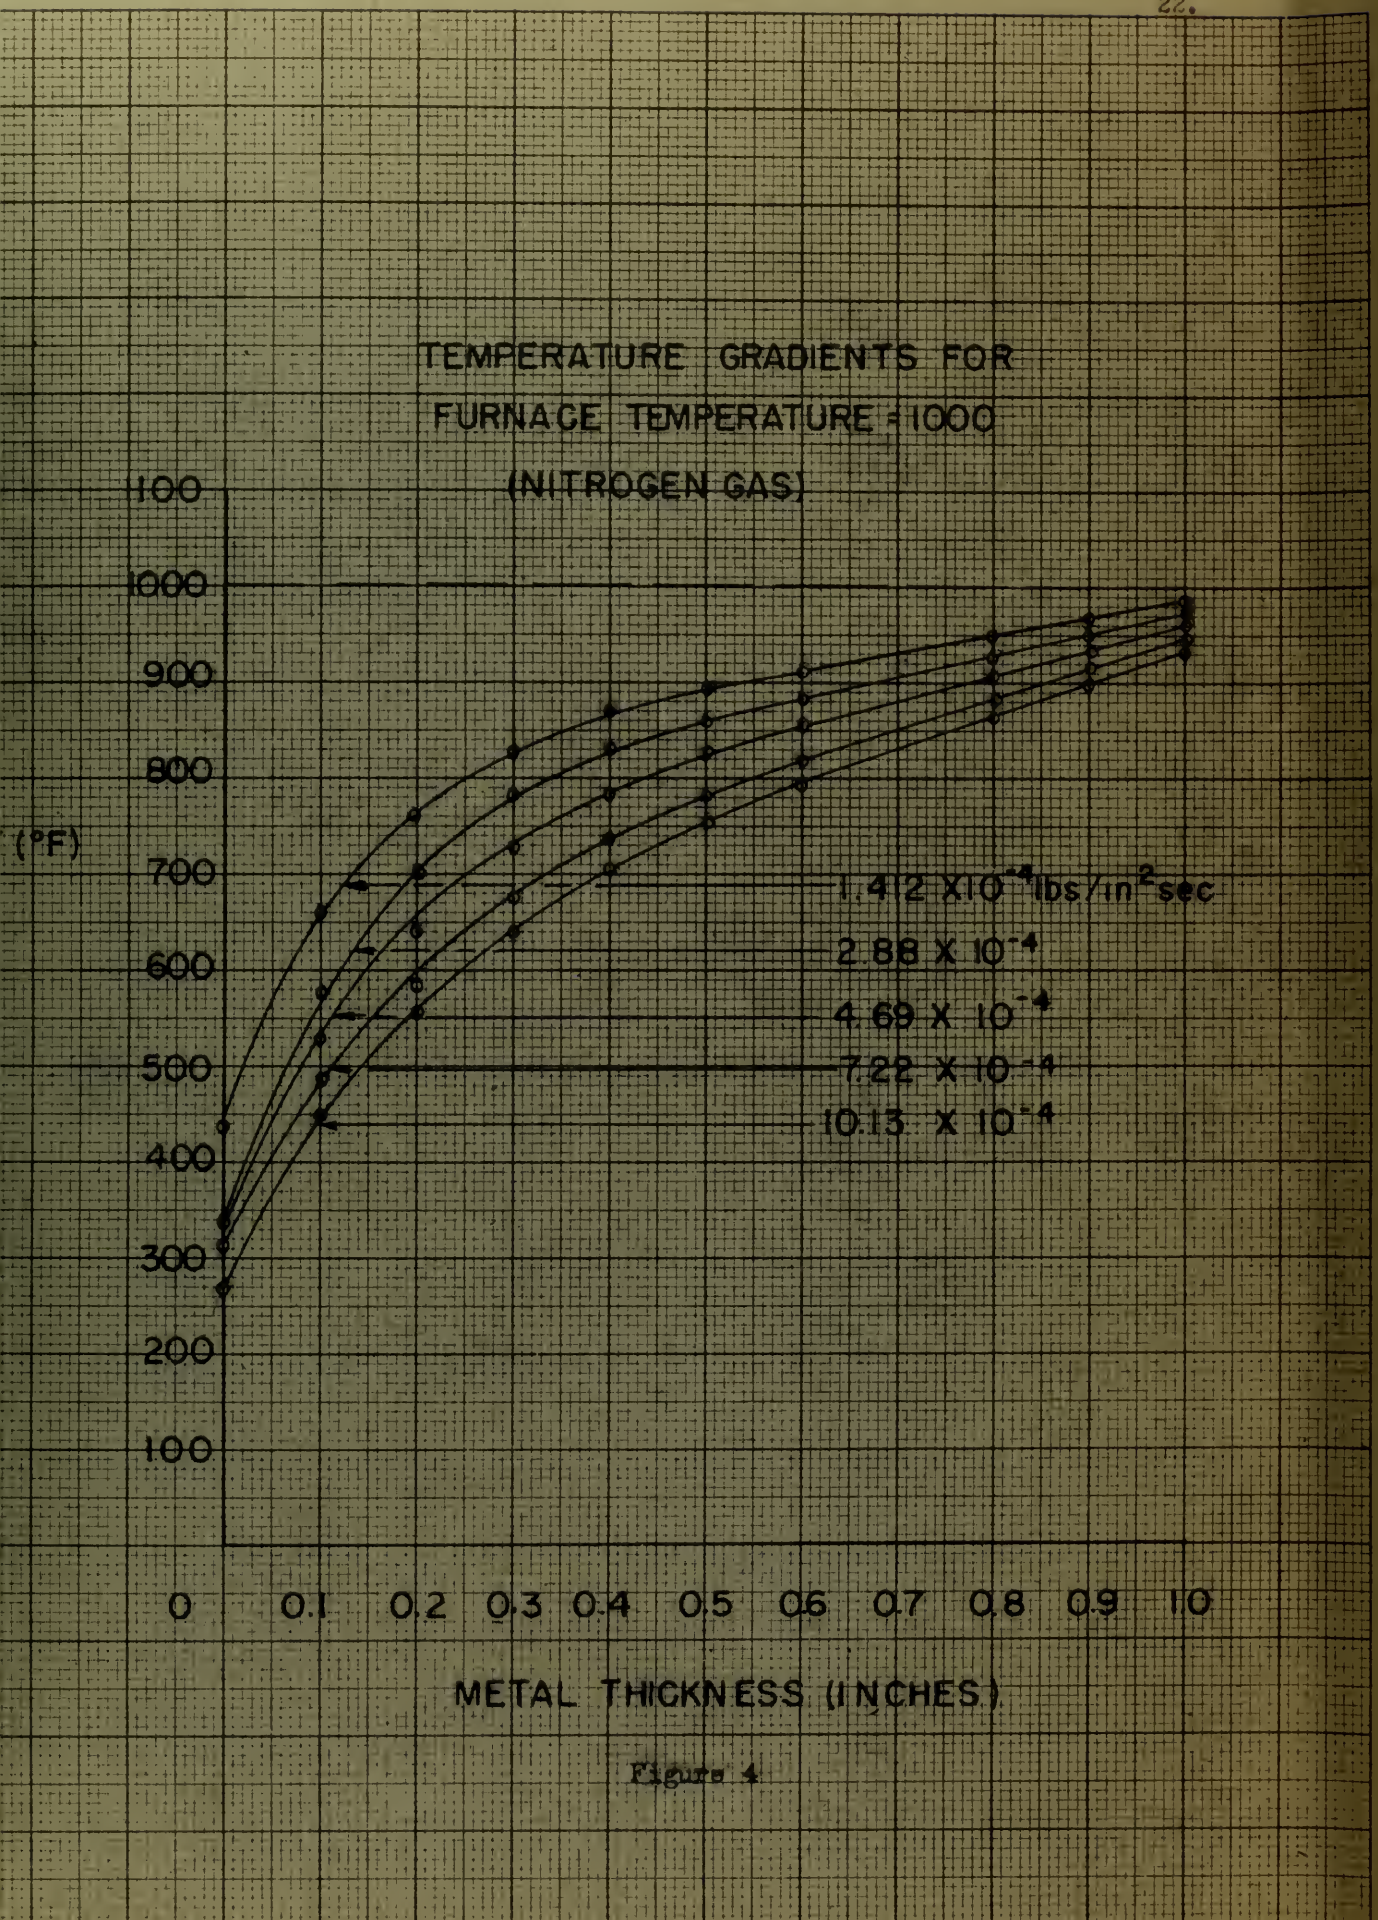
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 1000
(NITROGEN GAS)
1100
1000
900
800
(°F)
700
600
500
400
300
200
100
1.412 X10⁻⁴ lbs/in² sec
2.88 X 10⁻⁴
4.69 X 10⁻⁴
7.22 X 10⁻⁴
10.13 X 10⁻⁴
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 4

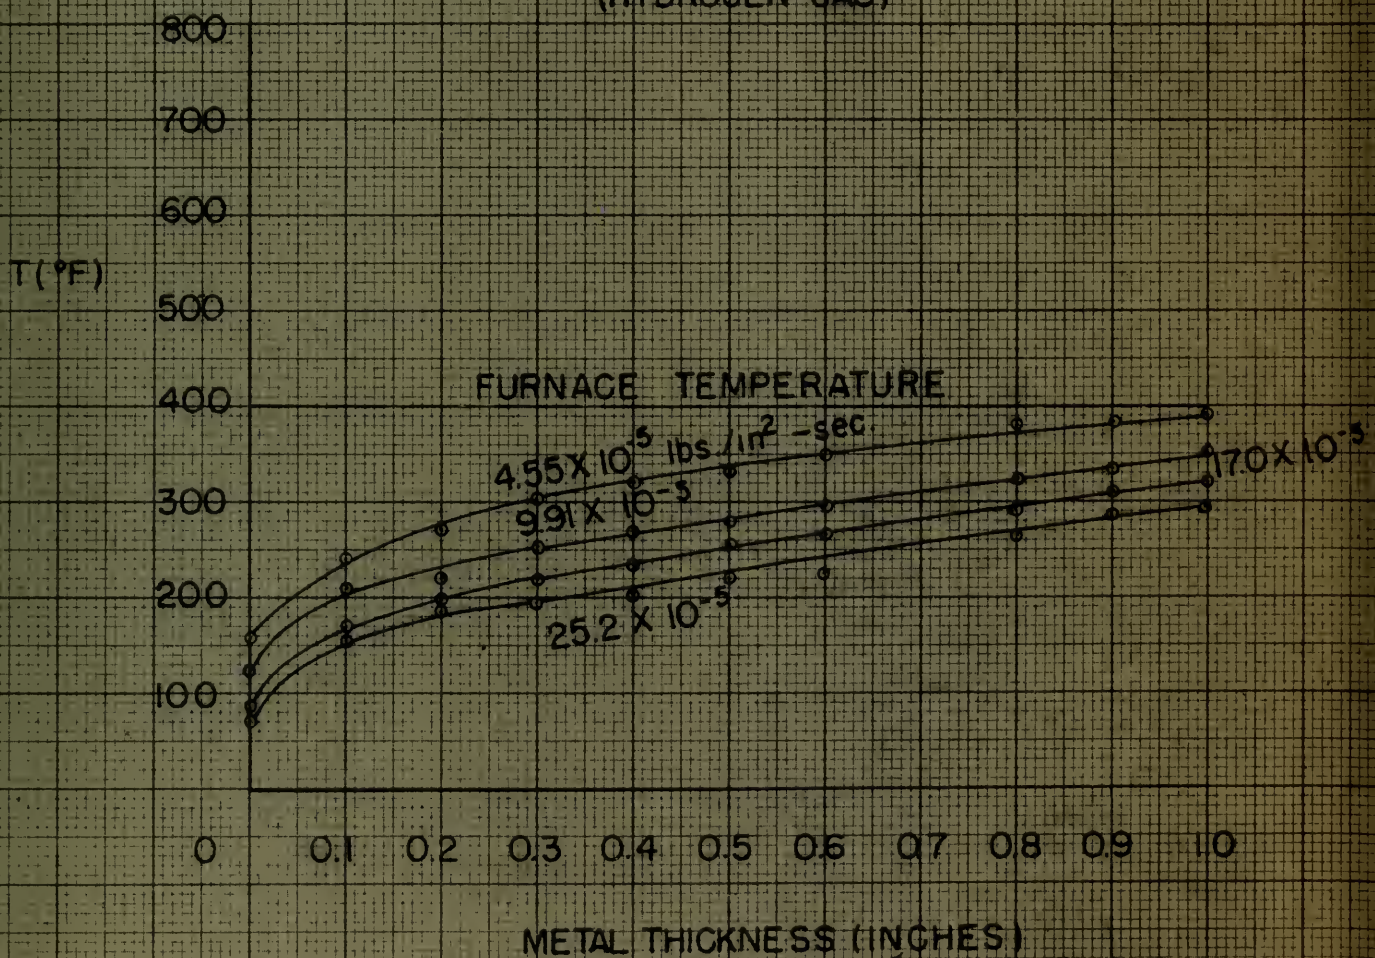
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 400 °F
(HYDROGEN GAS)
T(°F)
800
700
600
500
400
300
200
100
FURNACE TEMPERATURE
4.55 X 10^-5 lbs./in^2 -sec.
9.91 X 10^-5
17.0 X 10^-5
25.2 X 10^-5
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 5

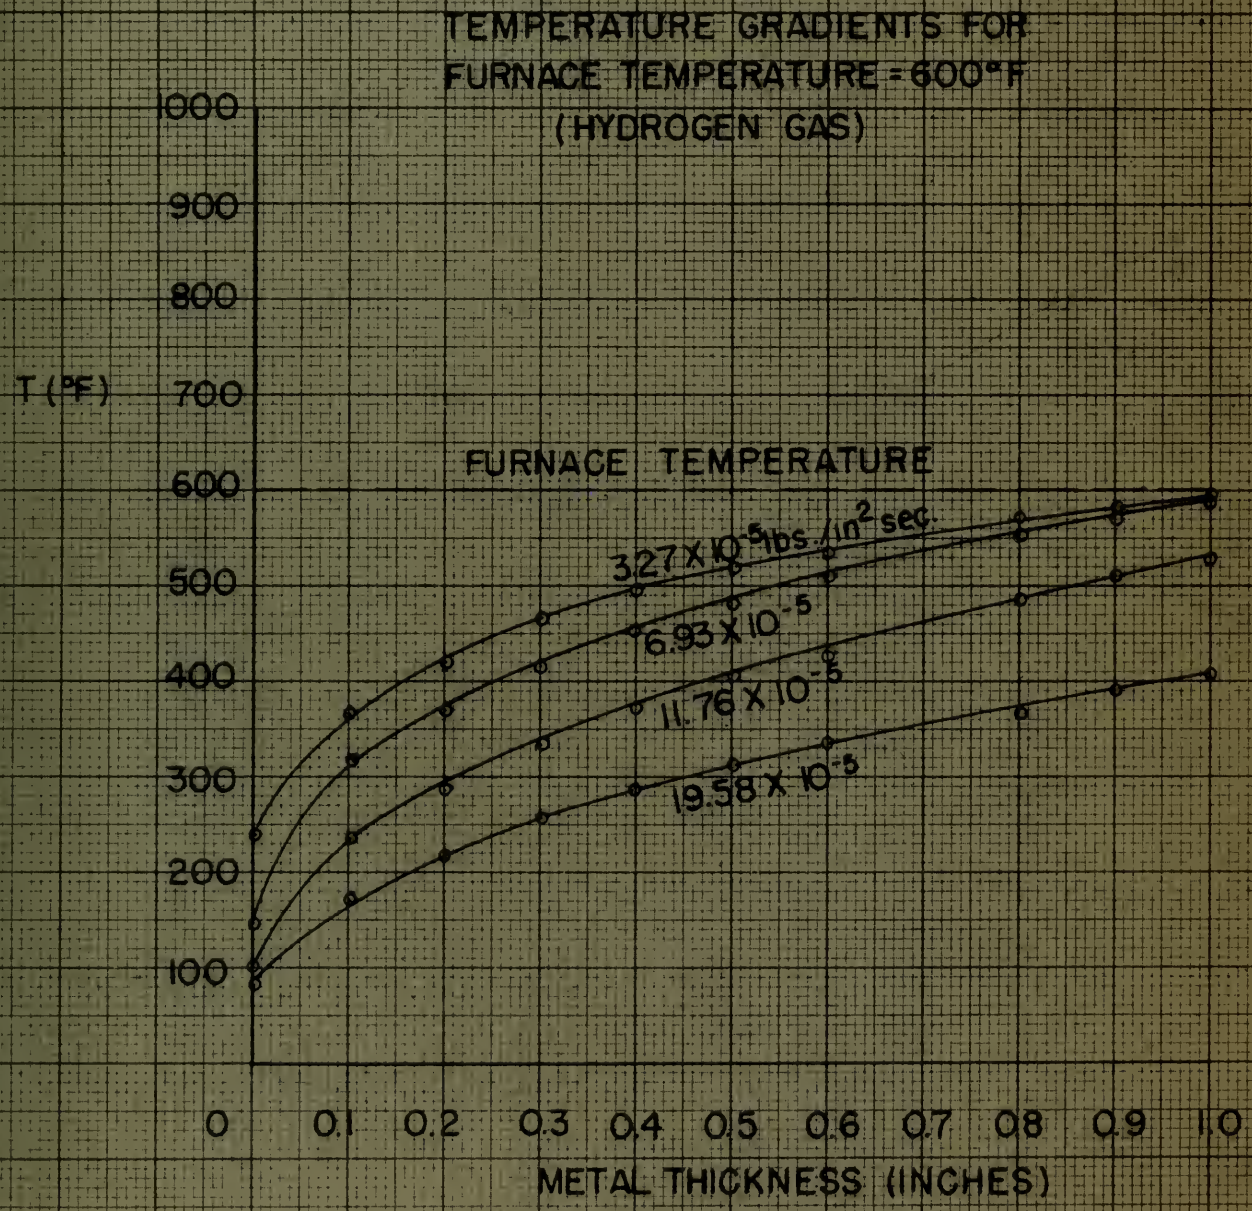
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 600°F
(HYDROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
FURNACE TEMPERATURE
3.27 X 10⁻⁵ lbs./in² sec.
6.93 X 10⁻⁵
11.76 X 10⁻⁵
19.58 X 10⁻⁵
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 6

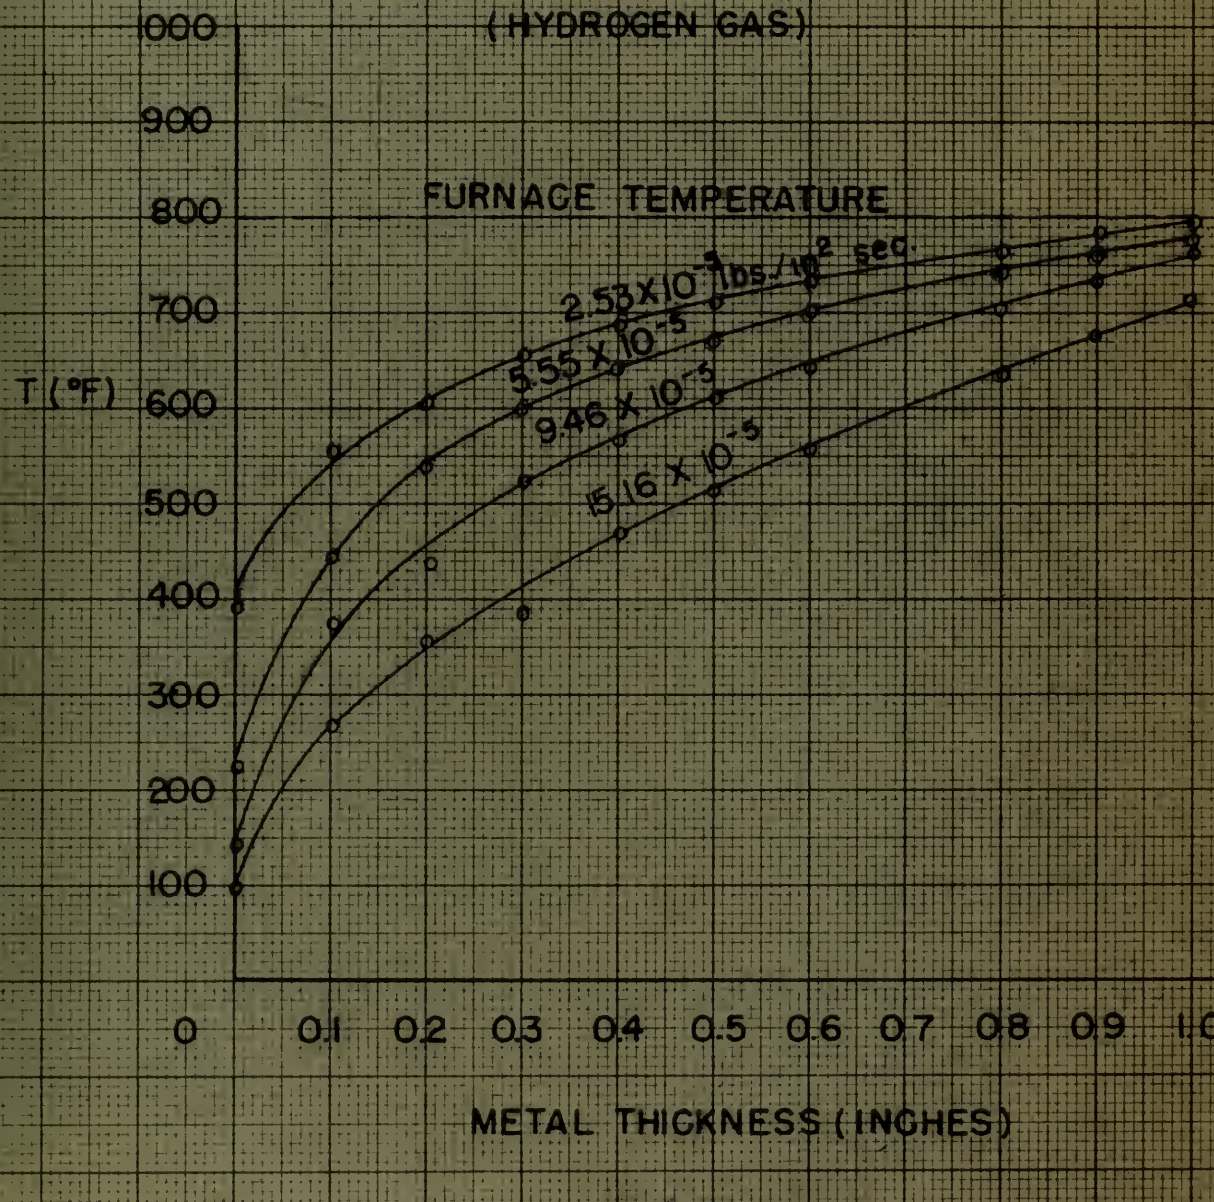
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE = 800°F
(HYDROGEN GAS)
FURNACE TEMPERATURE
T (°F)
1000
900
800
700
600
500
400
300
200
100
2.53 X 10⁻⁵ lbs./in² sec.
5.55 X 10⁻⁵
9.46 X 10⁻⁵
15.16 X 10⁻⁵
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 7

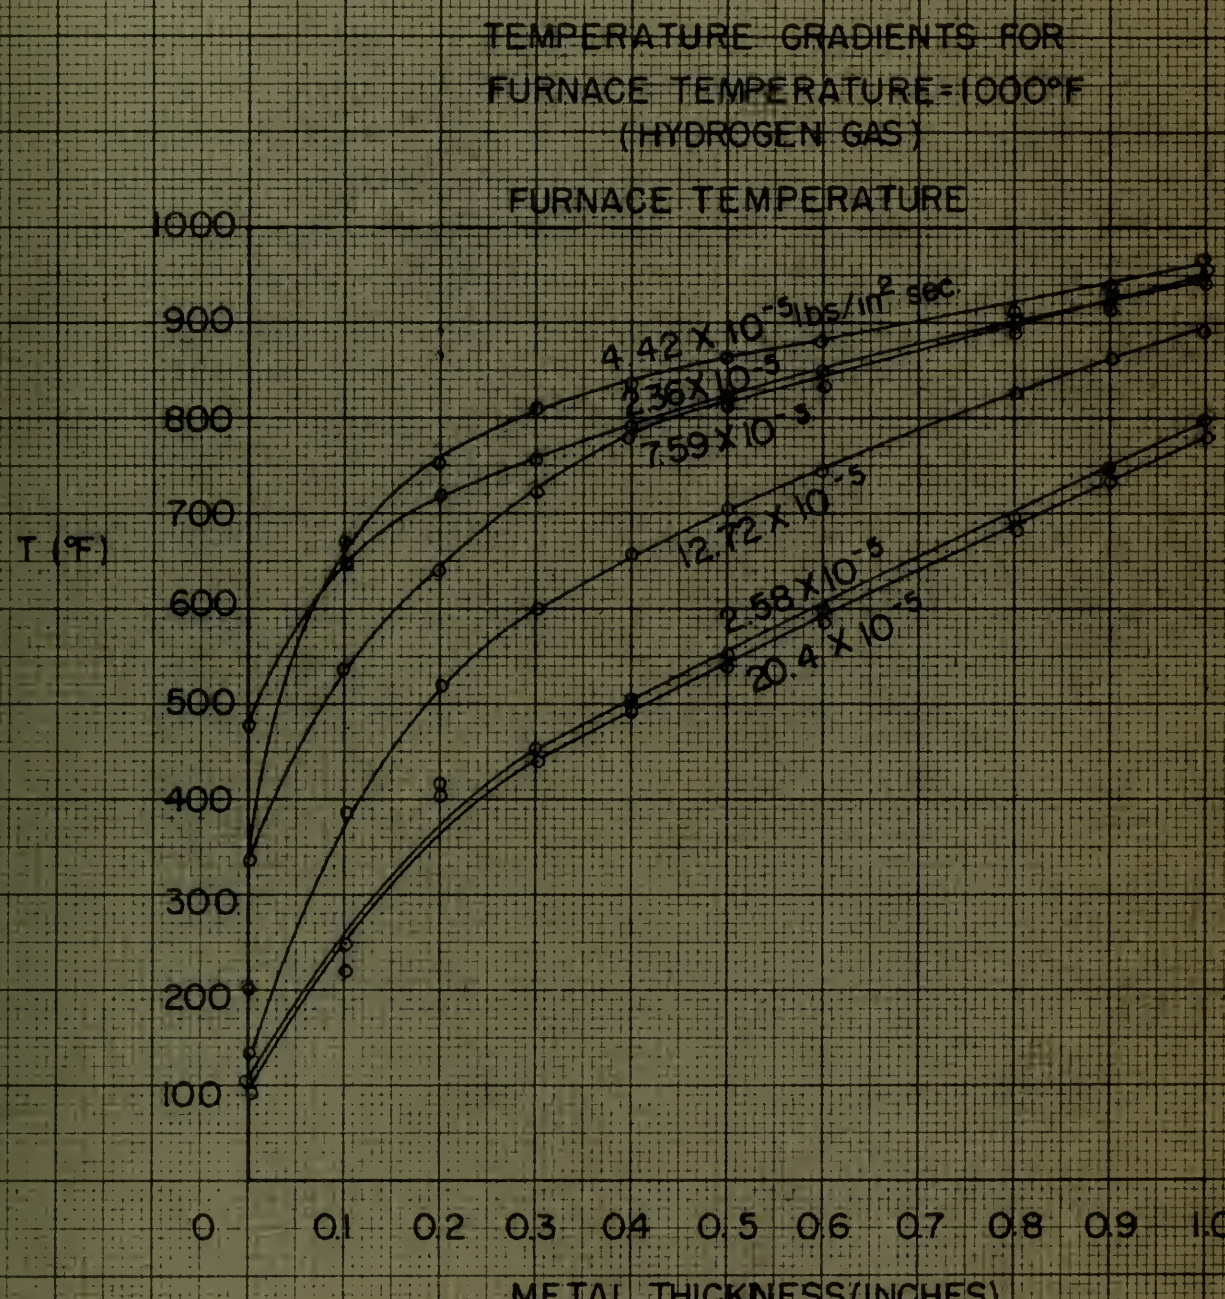
TEMPERATURE GRADIENTS FOR
FURNACE TEMPERATURE=1000°F
(HYDROGEN GAS)
FURNACE TEMPERATURE
T (°F)
1000
900
800
700
600
500
400
300
200
100
4.42 X 10⁻⁵ lbs/in² sec.
3.36 X 10⁻⁵
7.59 X 10⁻⁵
12.72 X 10⁻⁵
2.58 X 10⁻⁵
20.4 X 10⁻⁵
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS(INCHES)

Figure 8

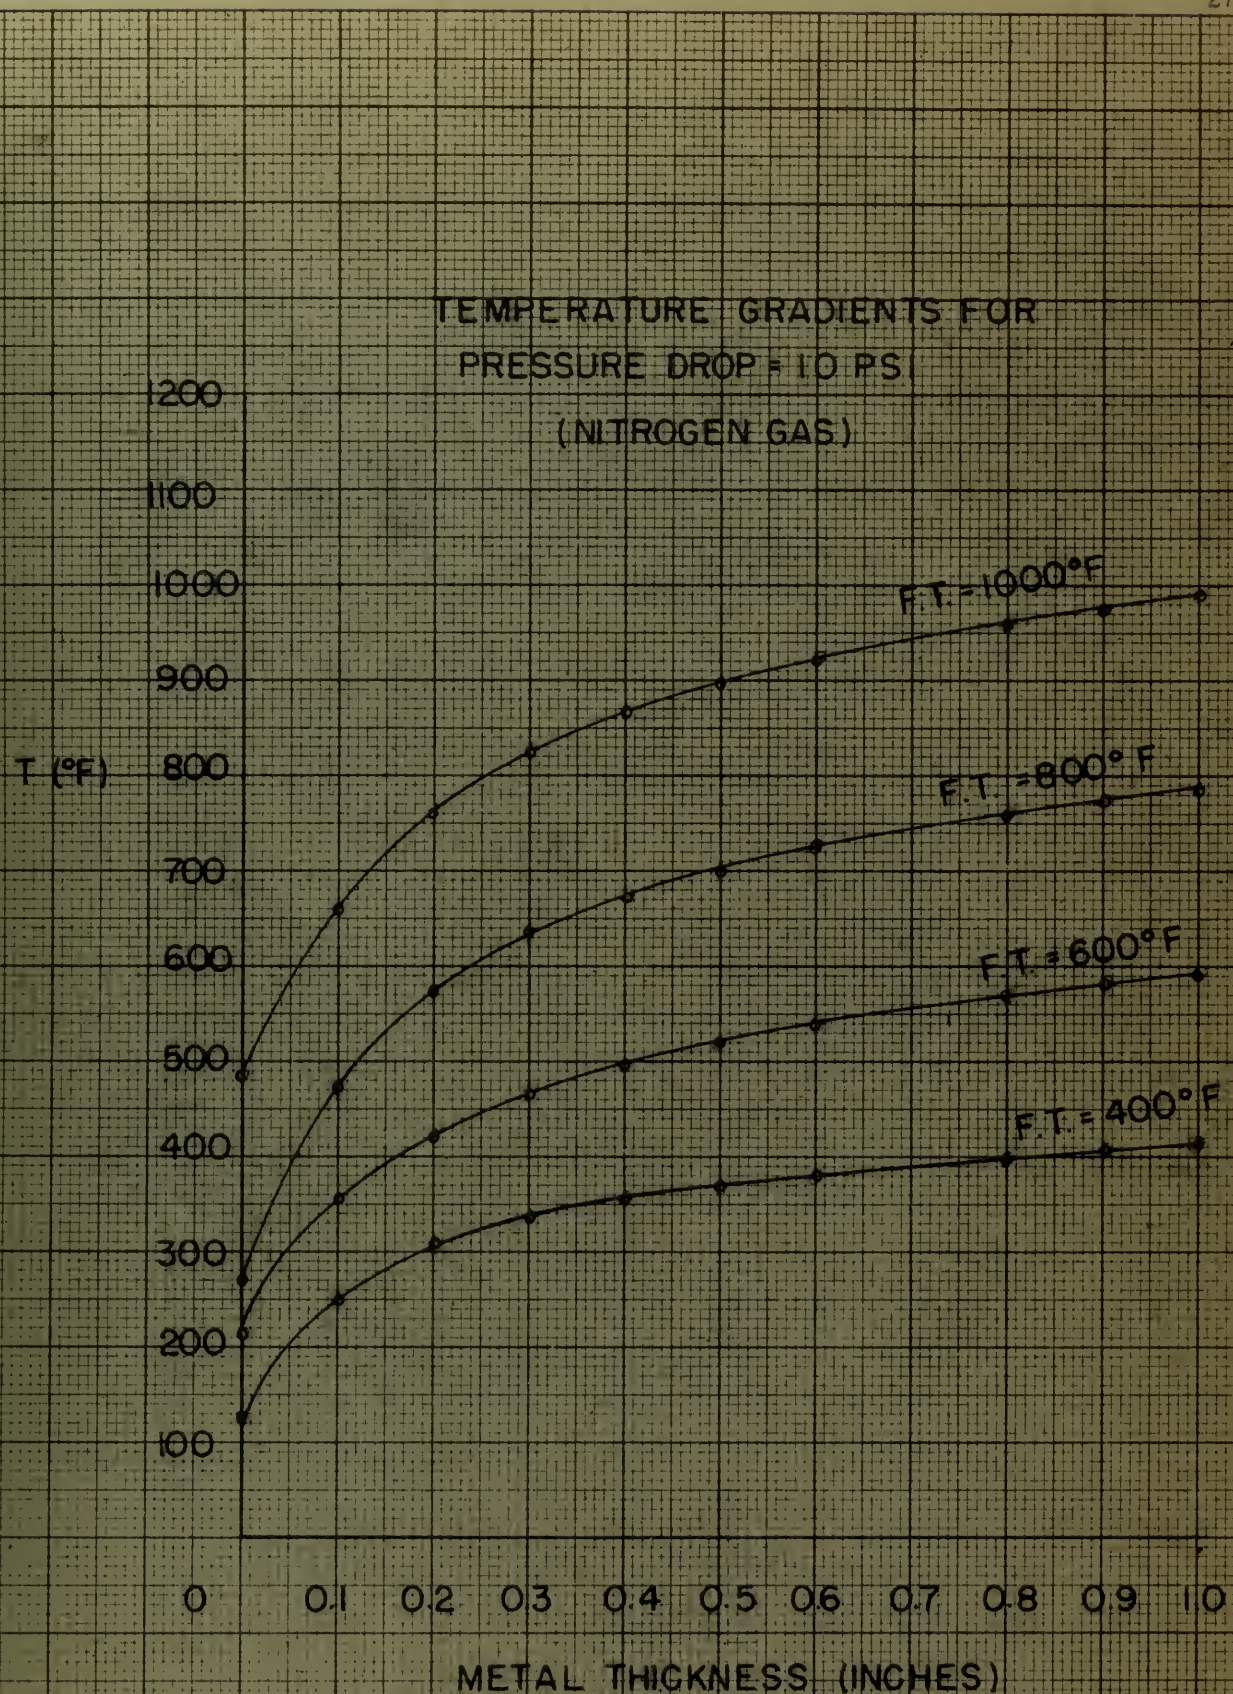
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 10 PSI
(NITROGEN GAS)
T (°F)
1200
1100
1000
900
800
700
600
500
400
300
200
100
F.T. = 1000° F
F.T. = 800° F
F.T. = 600° F
F.T. = 400° F
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 9

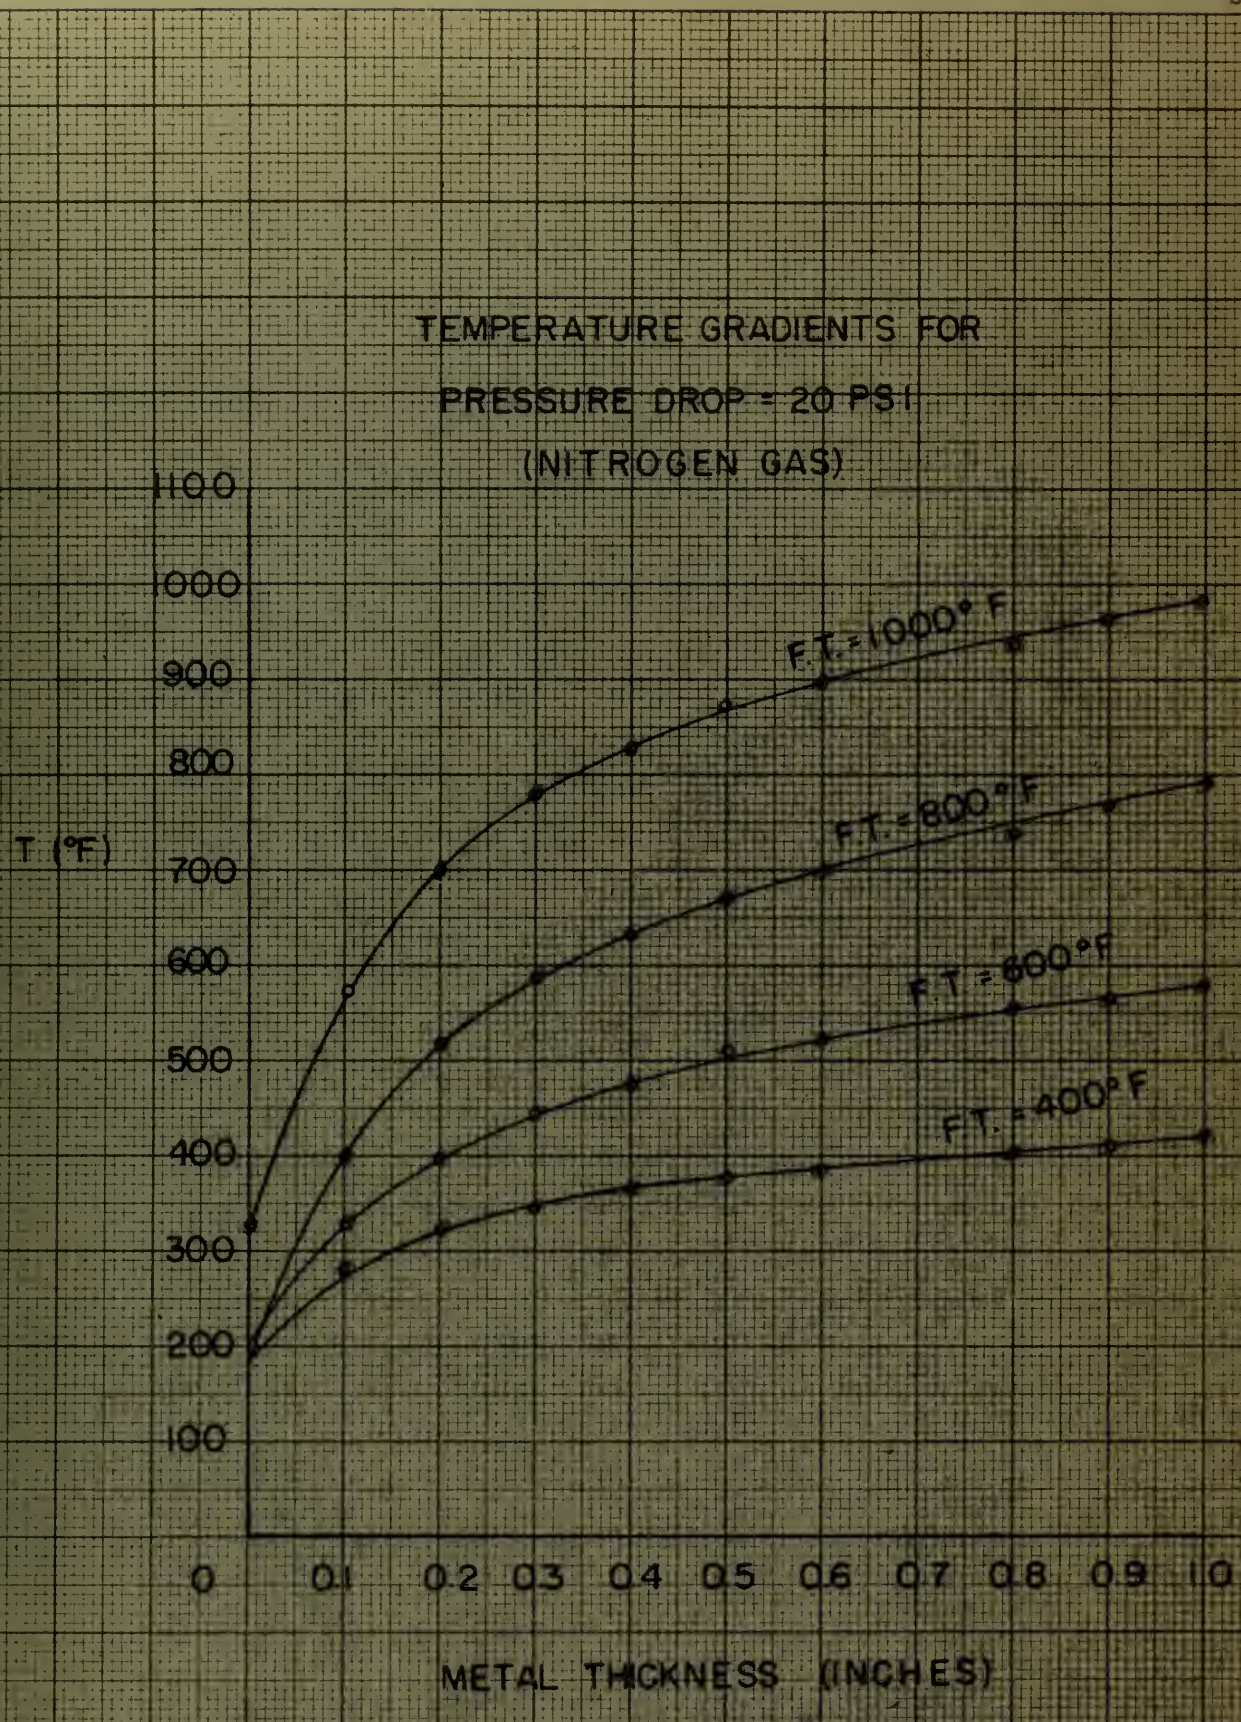
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 20 PSI
(NITROGEN GAS)
T (°F)
1100
1000
900
800
700
600
500
400
300
200
100
F.T. = 1000° F
F.T. = 800° F
F.T. = 600° F
F.T. = 400° F
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 10

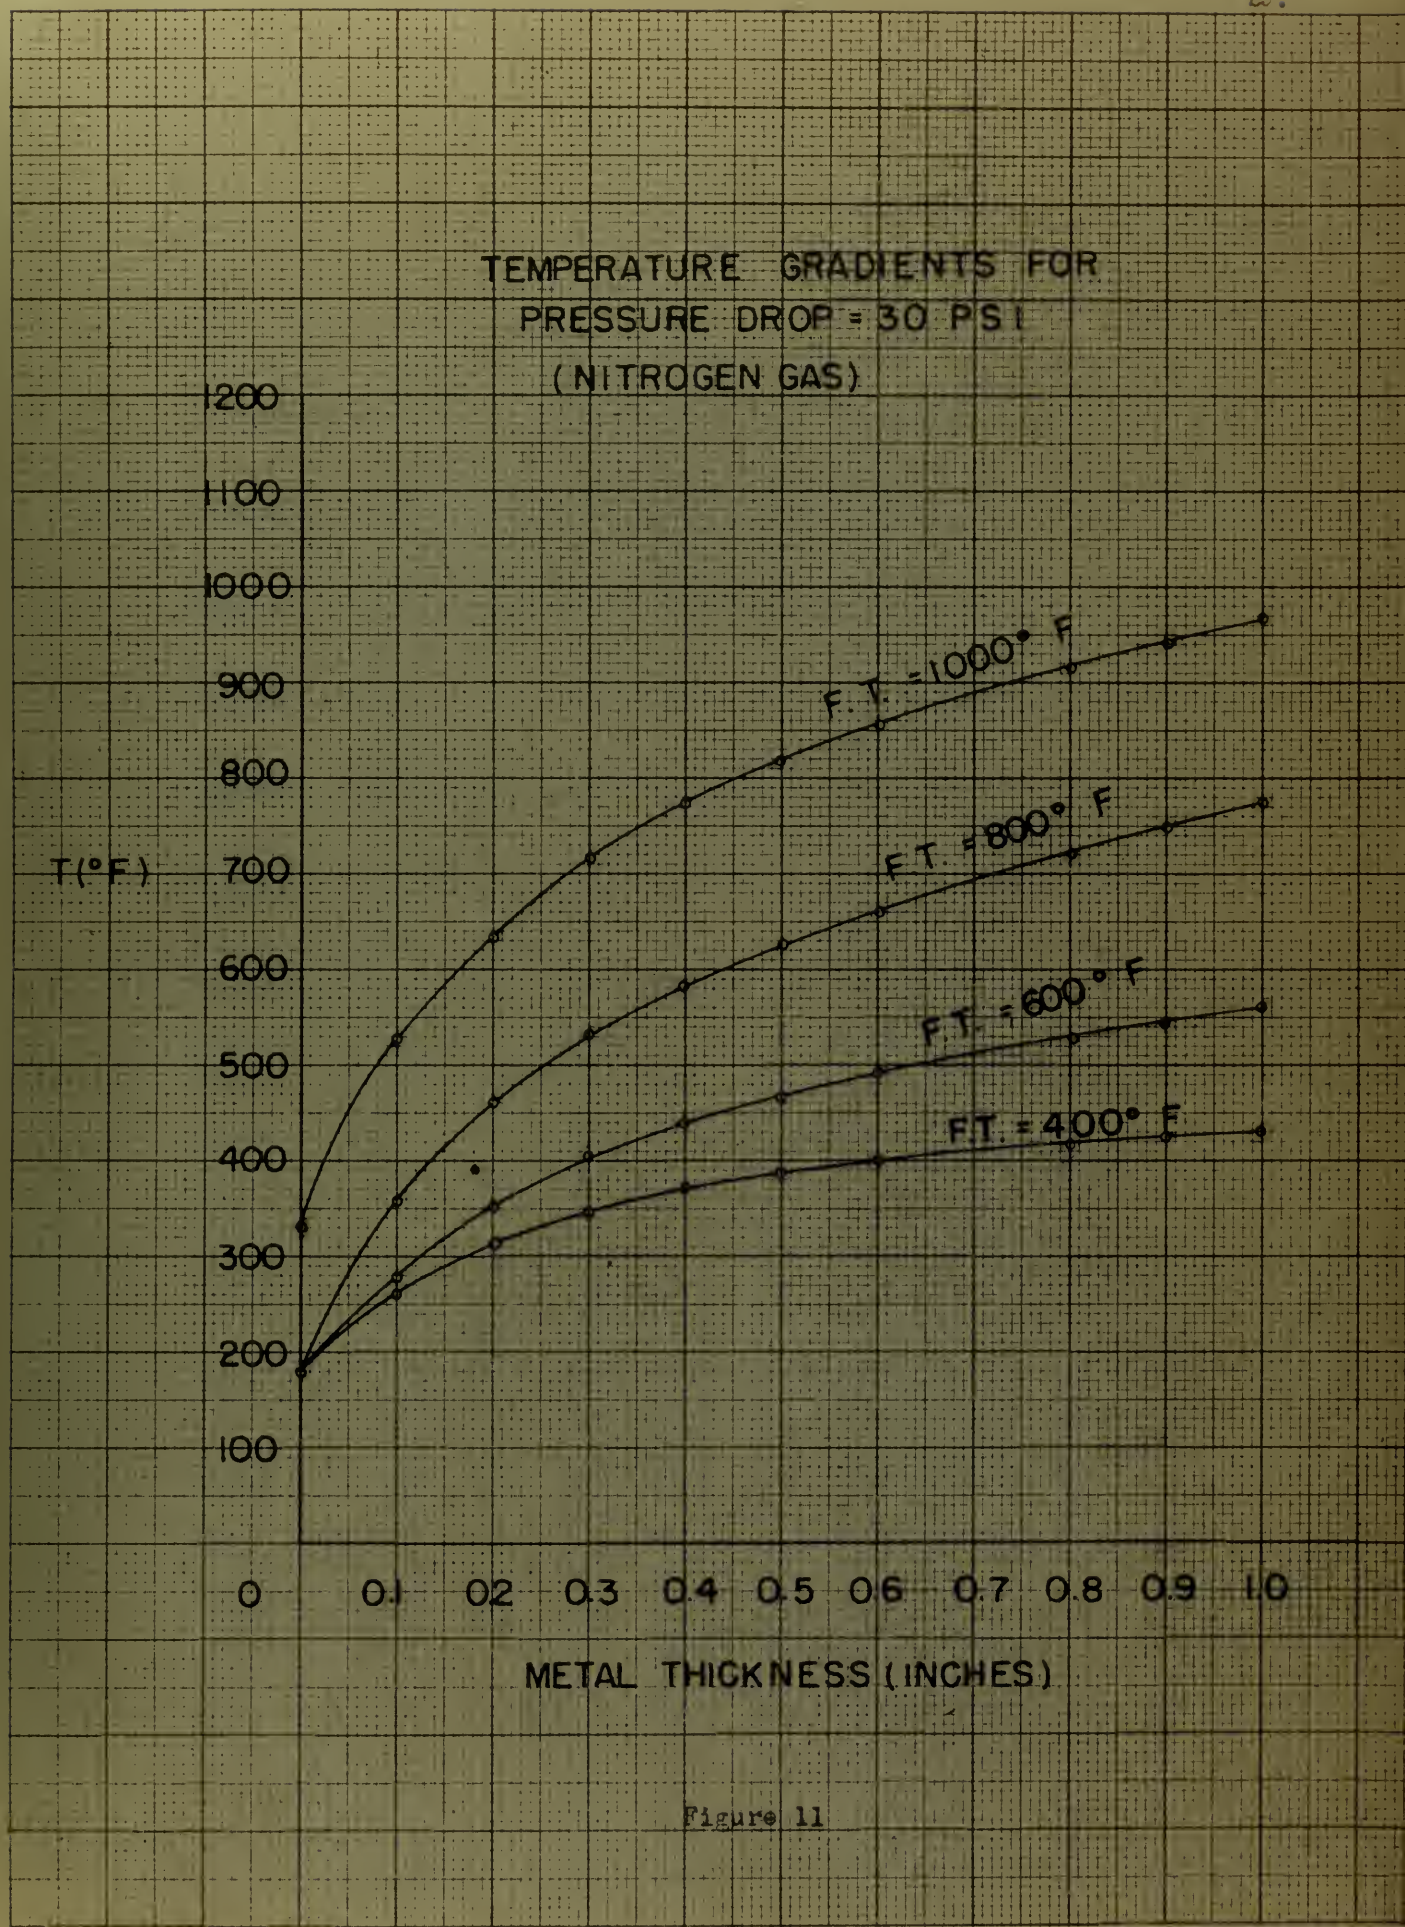
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 30 PSI
(NITROGEN GAS)
T(°F)
1200
1100
1000
900
800
700
600
500
400
300
200
100
F.T. = 1000° F
F.T. = 800° F
F.T. = 600° F
F.T. = 400° F
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 11

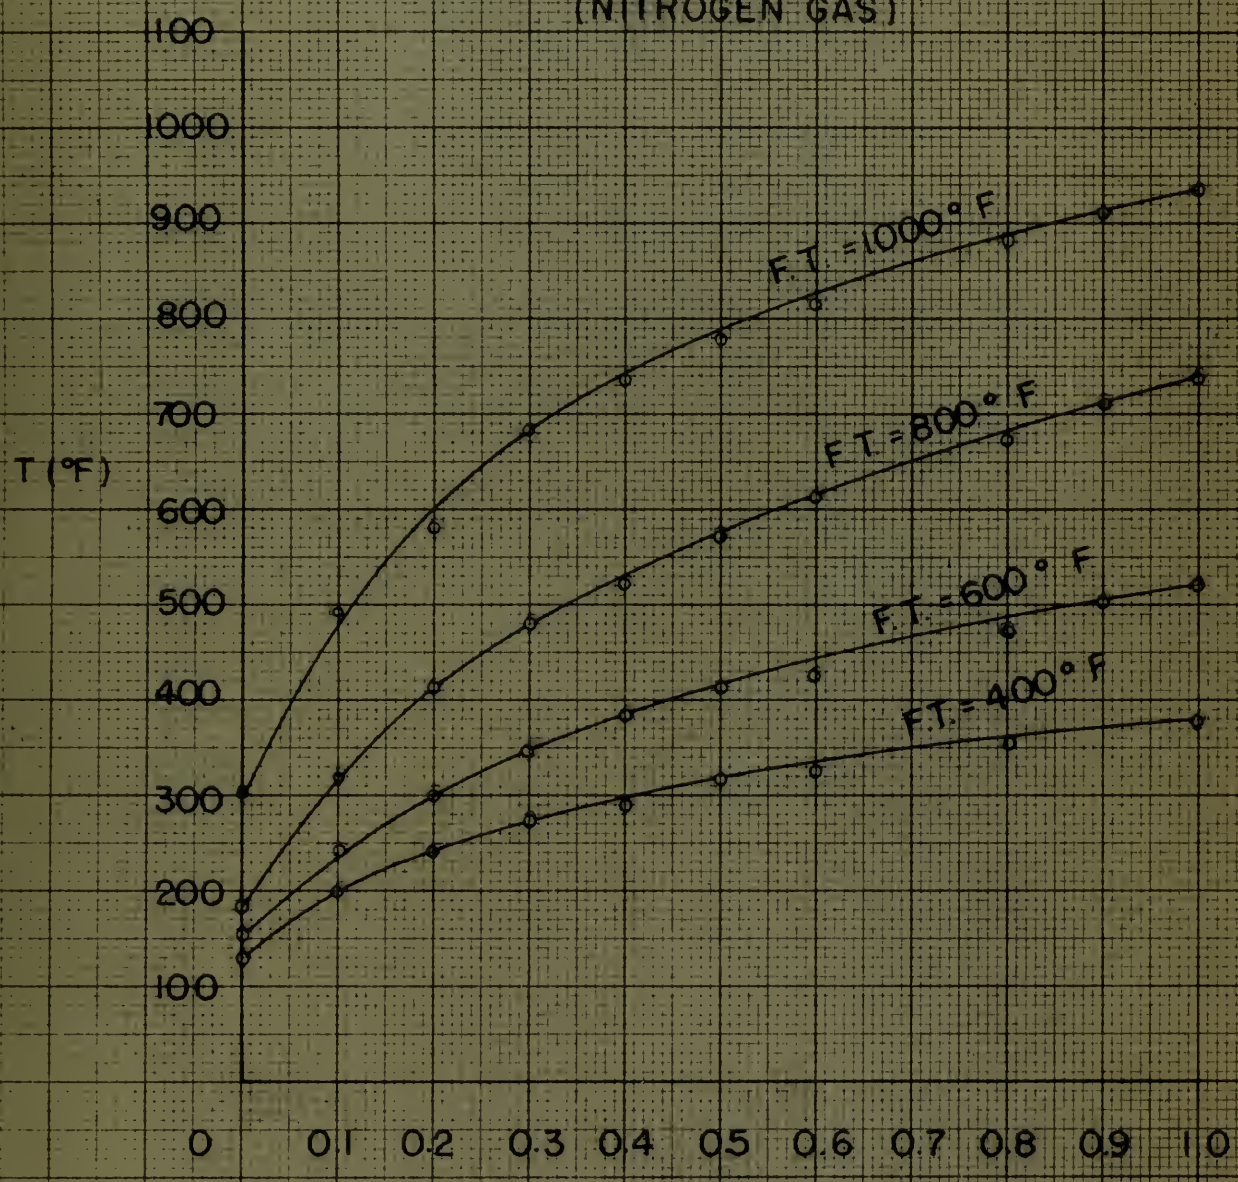
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 4.0 PSI
(NITROGEN GAS)
T (°F)
1100
1000
900
800
700
600
500
400
300
200
100
F.T. = 1000° F
F.T. = 800° F
F.T. = 600° F
F.T. = 400° F
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 12

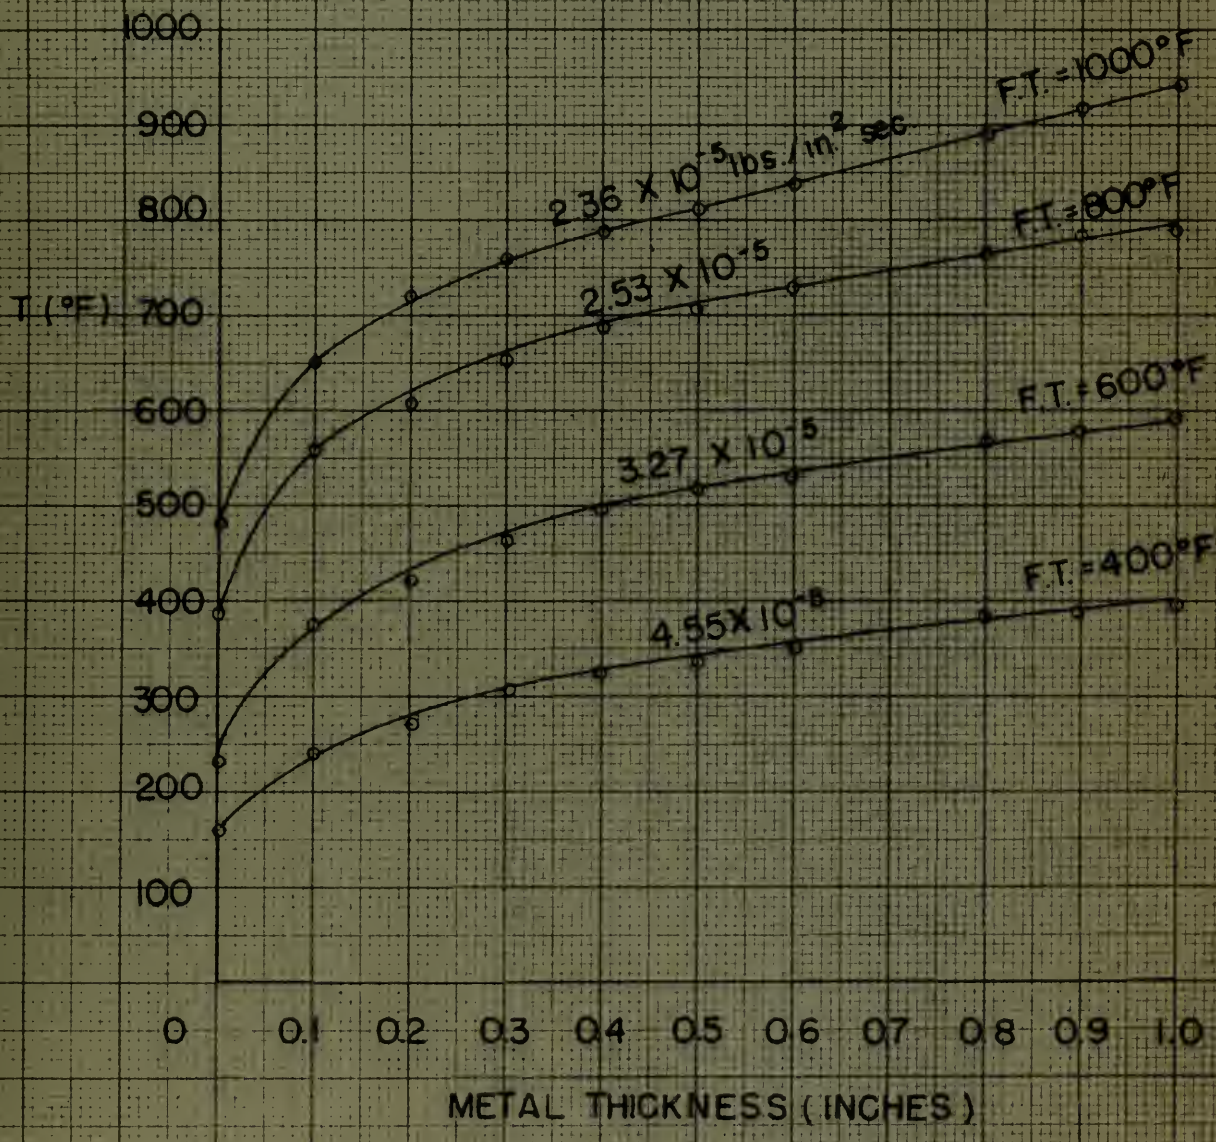
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 10 P.S.I
(HYDROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
F.T. = 1000°F
2.36 X 10⁻⁵ lbs./in² sec
F.T. = 800°F
2.53 X 10⁻⁵
F.T. = 600°F
3.27 X 10⁻⁵
F.T. = 400°F
4.55 X 10⁻⁵

Figure 13

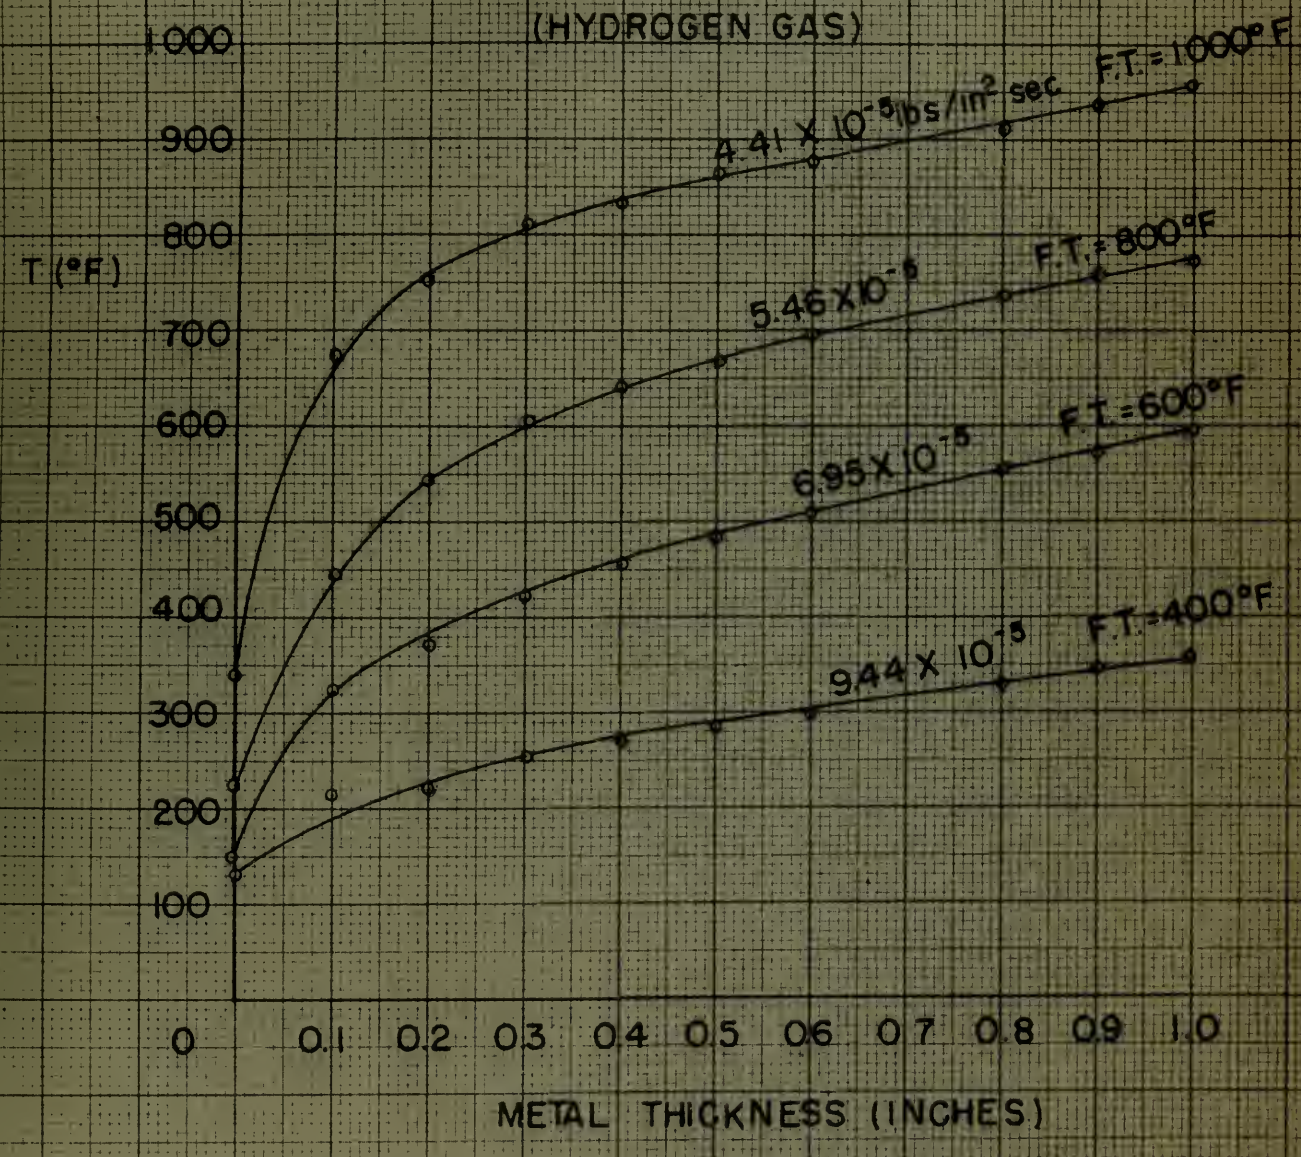
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 20 PSI
(HYDROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
4.41 X 10⁻⁵ lbs/in² sec
F.T. = 1000°F
5.46 X 10⁻⁵
F.T. = 800°F
6.95 X 10⁻⁵
F.T. = 600°F
9.44 X 10⁻⁵
F.T. = 400°F

Figure 14

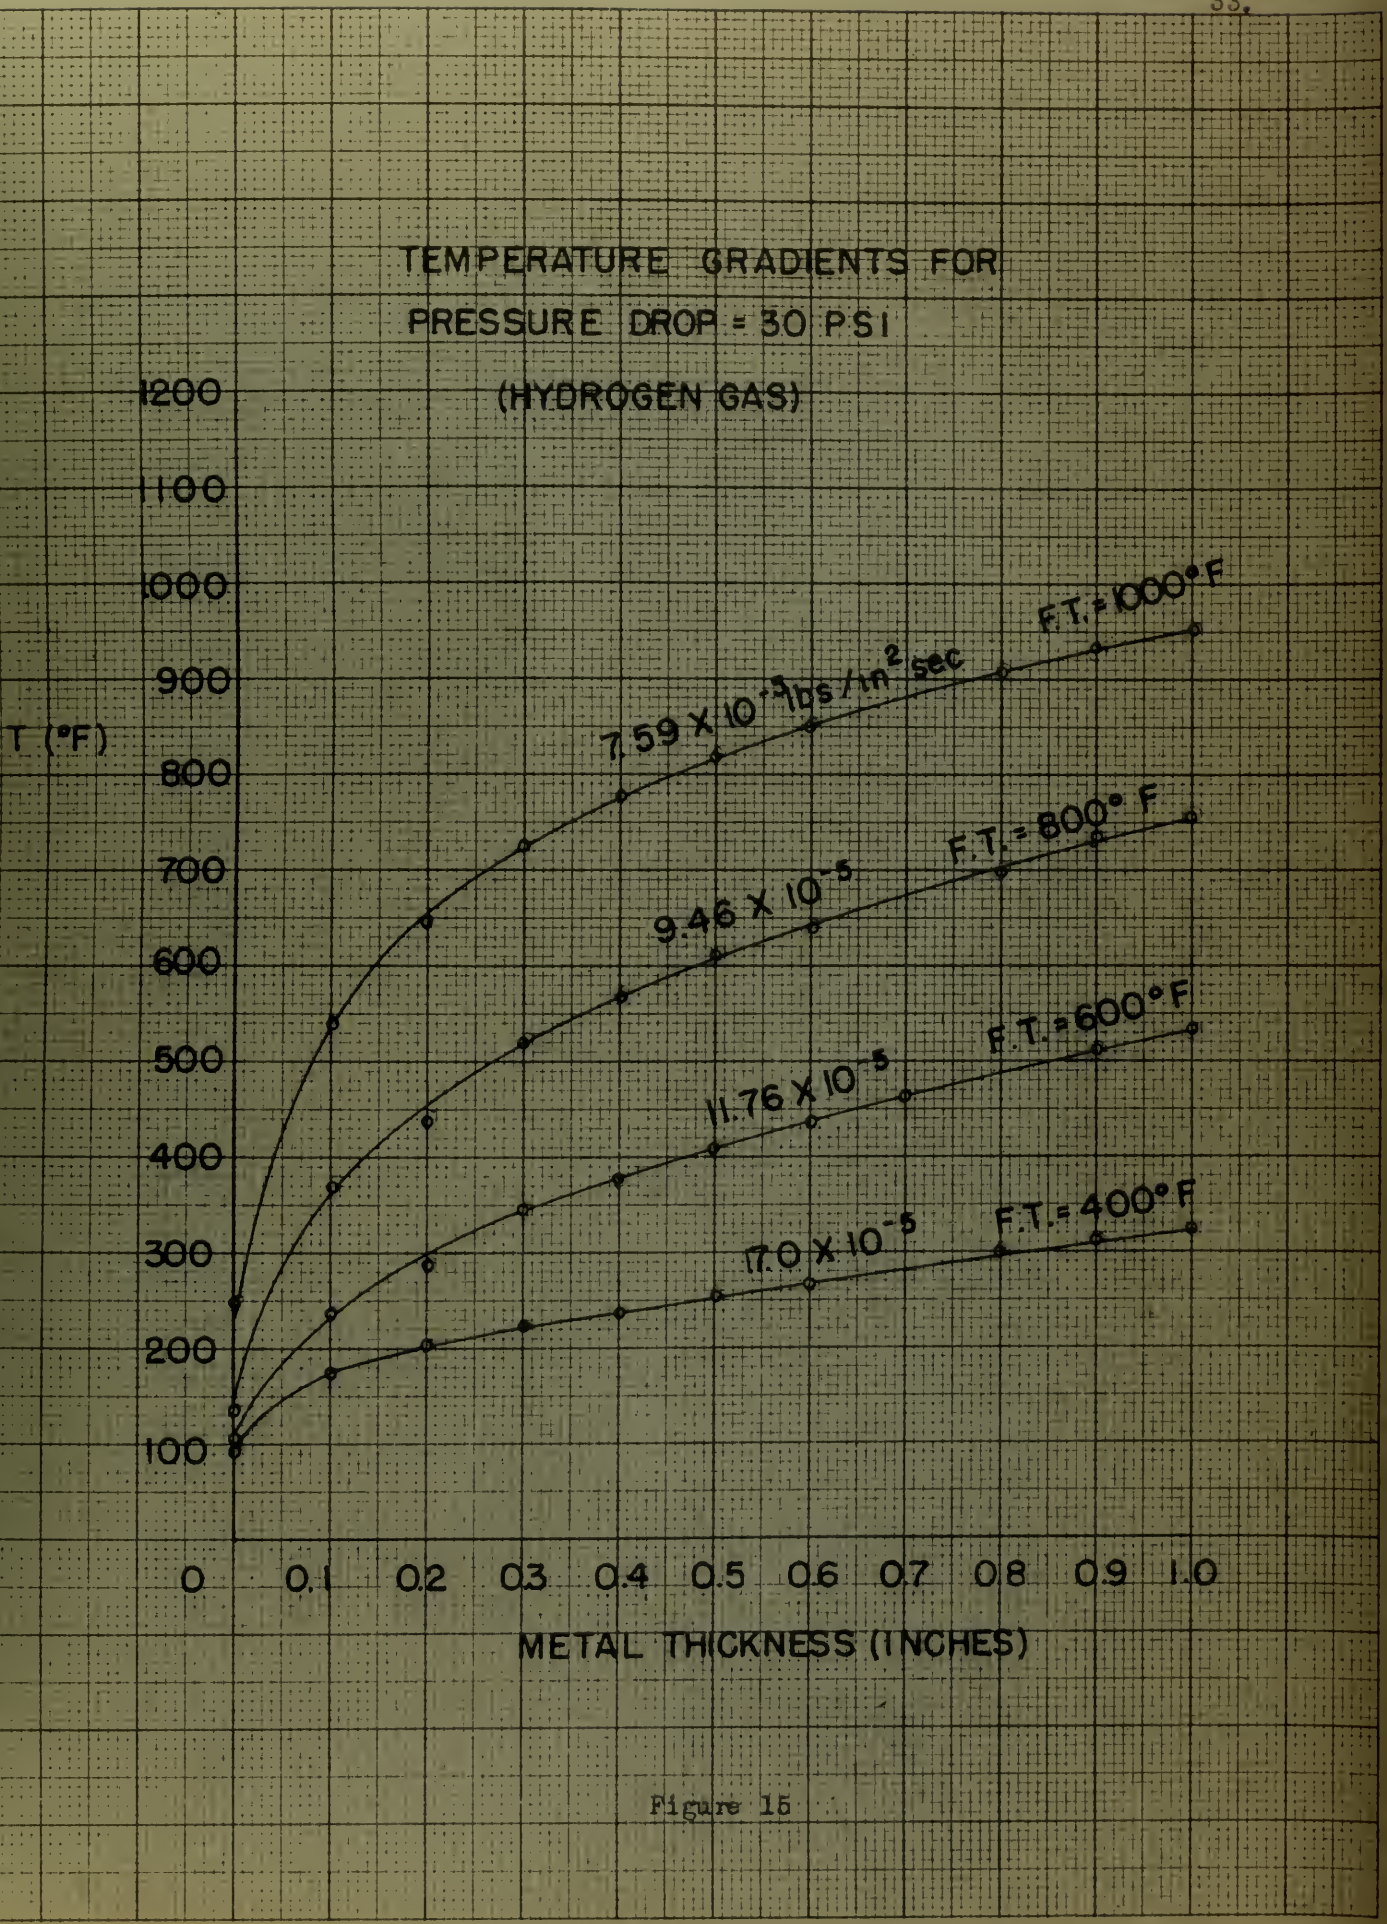
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 30 PSI
(HYDROGEN GAS)
T (°F)
1200
1100
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
7.59 X 10⁻⁵ lbs/in² sec
F.T. = 1000° F
9.46 X 10⁻⁵
F.T. = 800° F
11.76 X 10⁻⁵
F.T. = 600° F
17.0 X 10⁻⁵
F.T. = 400° F

Figure 15

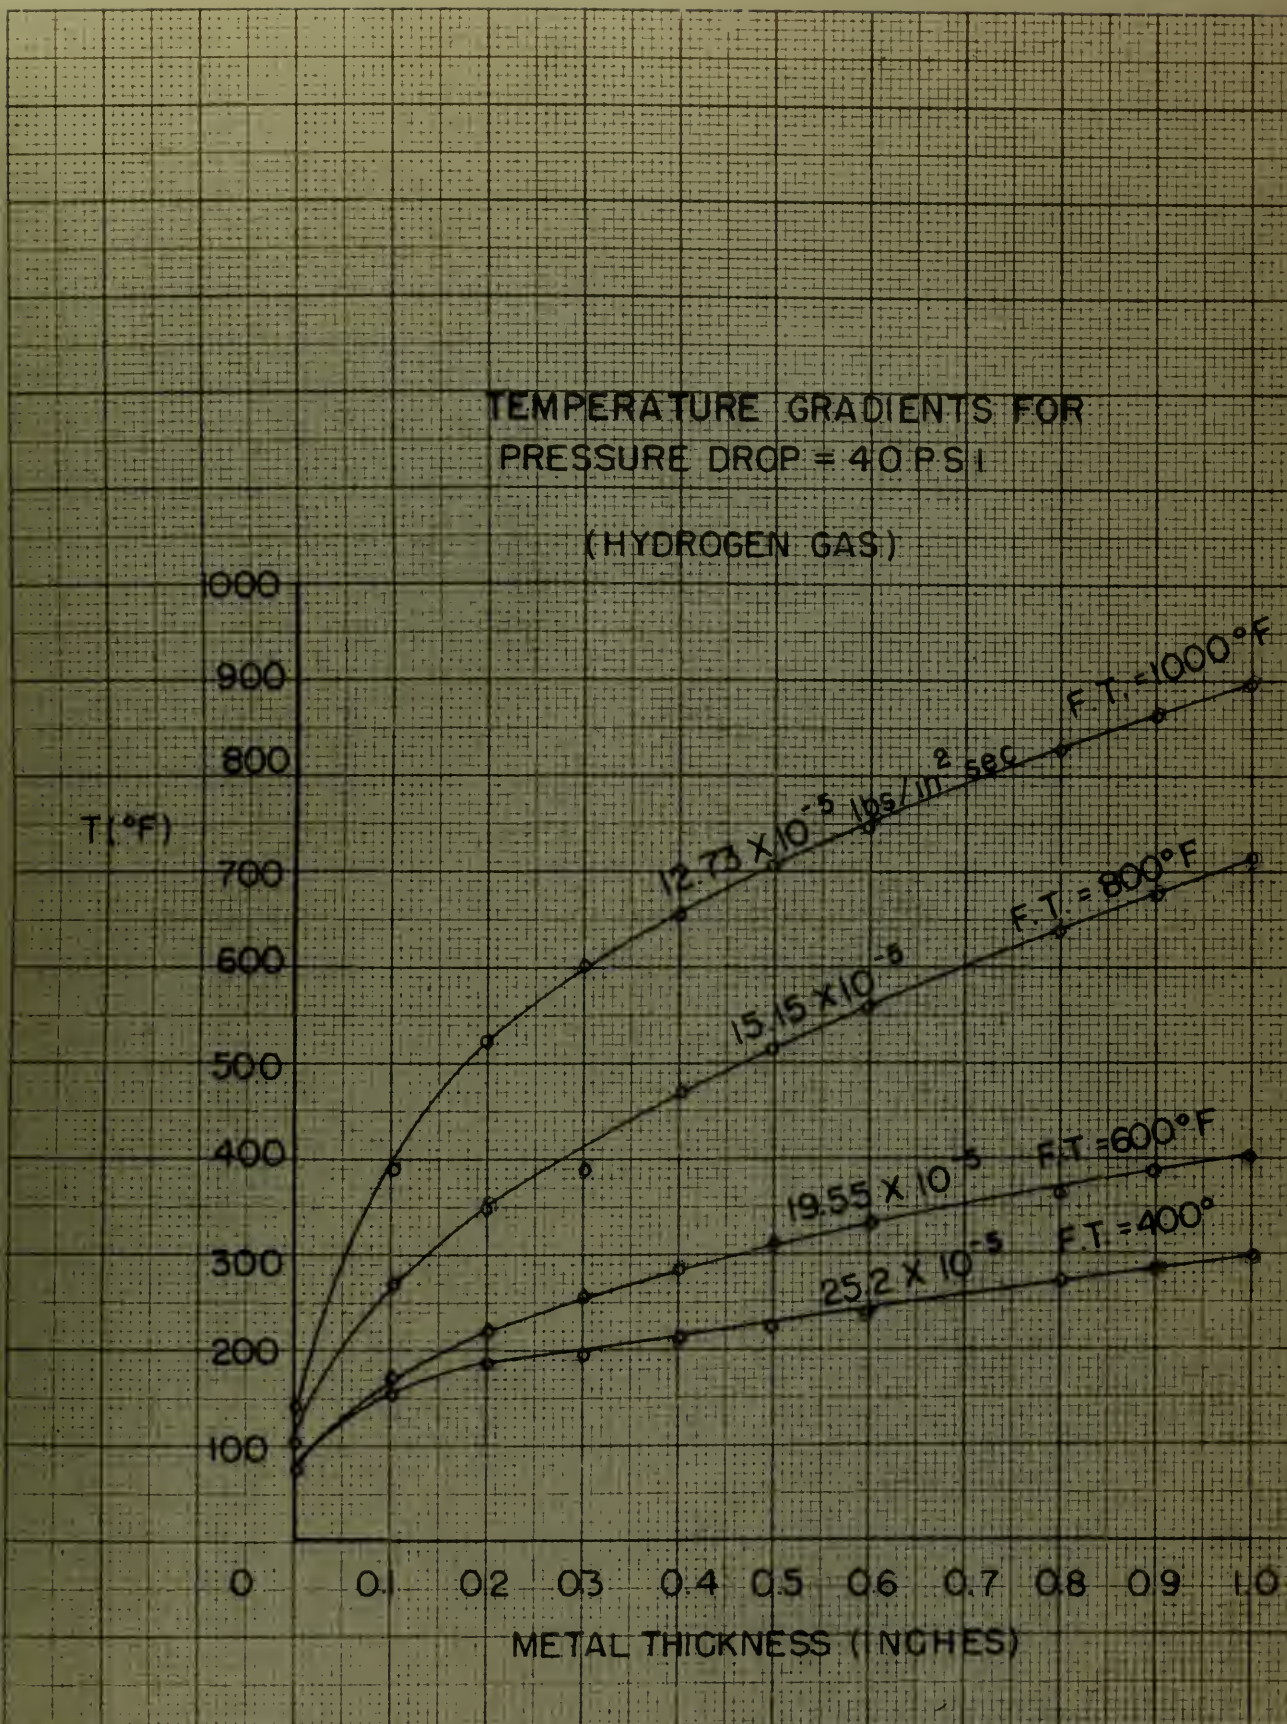
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 40 PSI
(HYDROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
12.73 X 10⁻⁵ lbs/in² sec
F.T. = 1000°F
15.15 X 10⁻⁵
F.T. = 800°F
19.55 X 10⁻⁵
F.T. = 600°F
25.2 X 10⁻⁵
F.T. = 400°

Figure 16

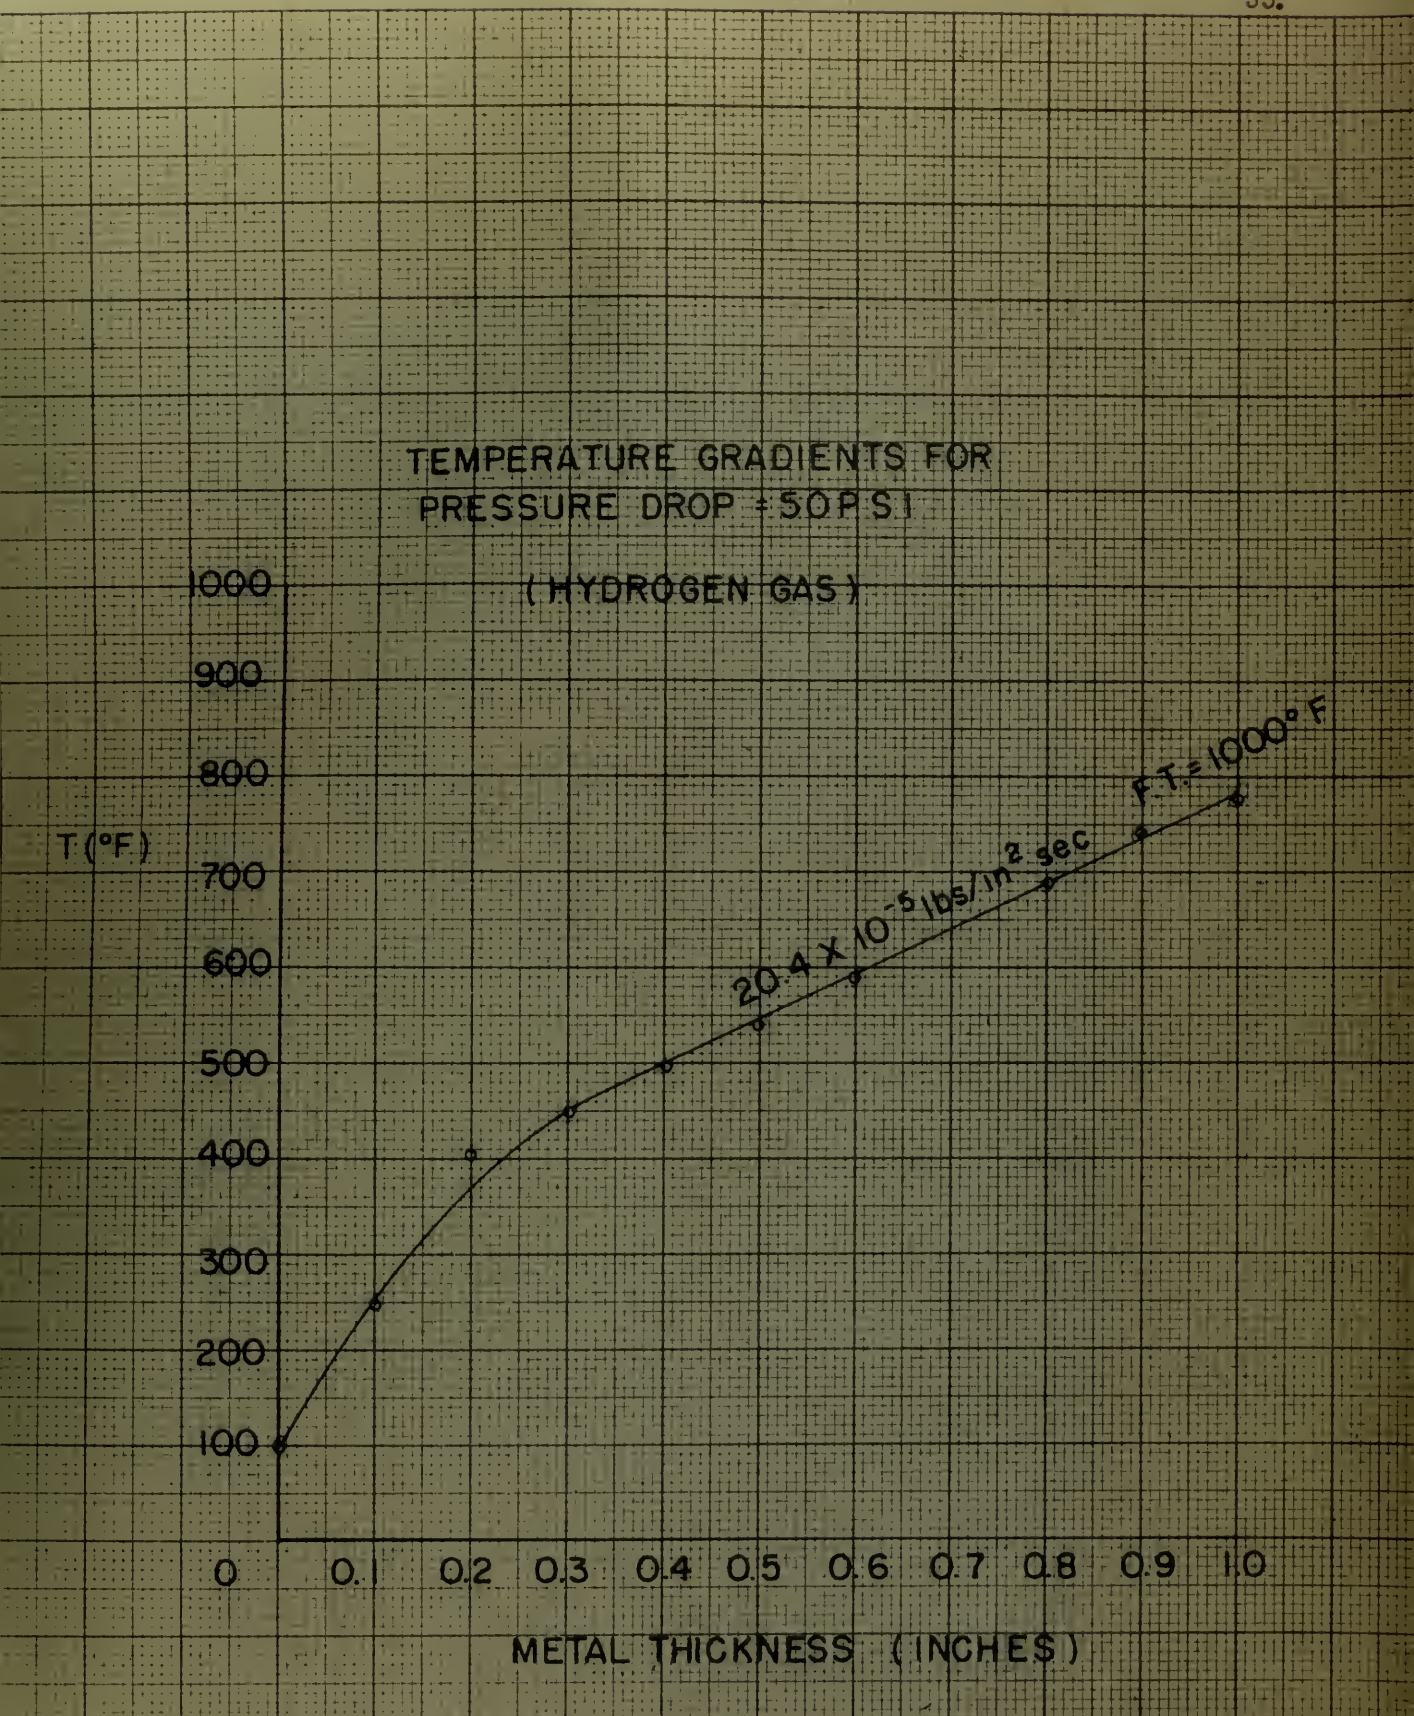
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 50 P.S.I.
(HYDROGEN GAS)
T(°F)
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
20.4 X 10⁻⁵ lbs/in² sec
F.T. = 1000° F

Figure 17

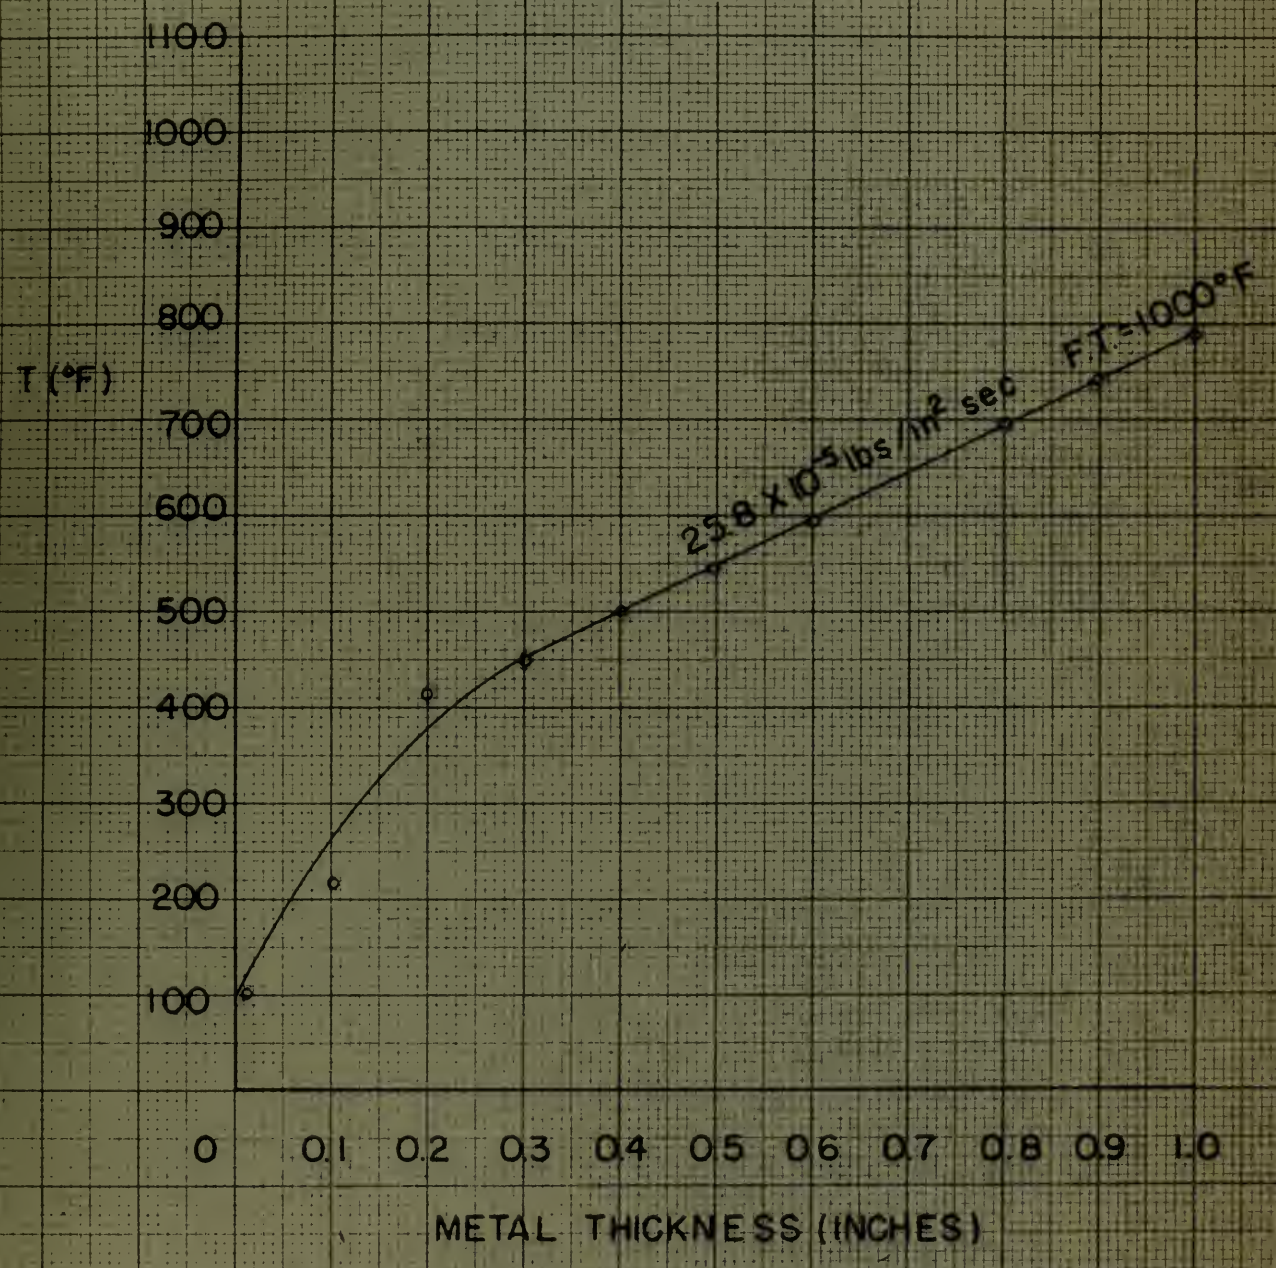
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 60 PSI
(HYDROGEN GAS)
T (°F)
1100
1000
900
800
700
600
500
400
300
200
100
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)
25.8 X 10⁻⁵ lbs/in² sec
F.T. = 1000°F

Figure 18

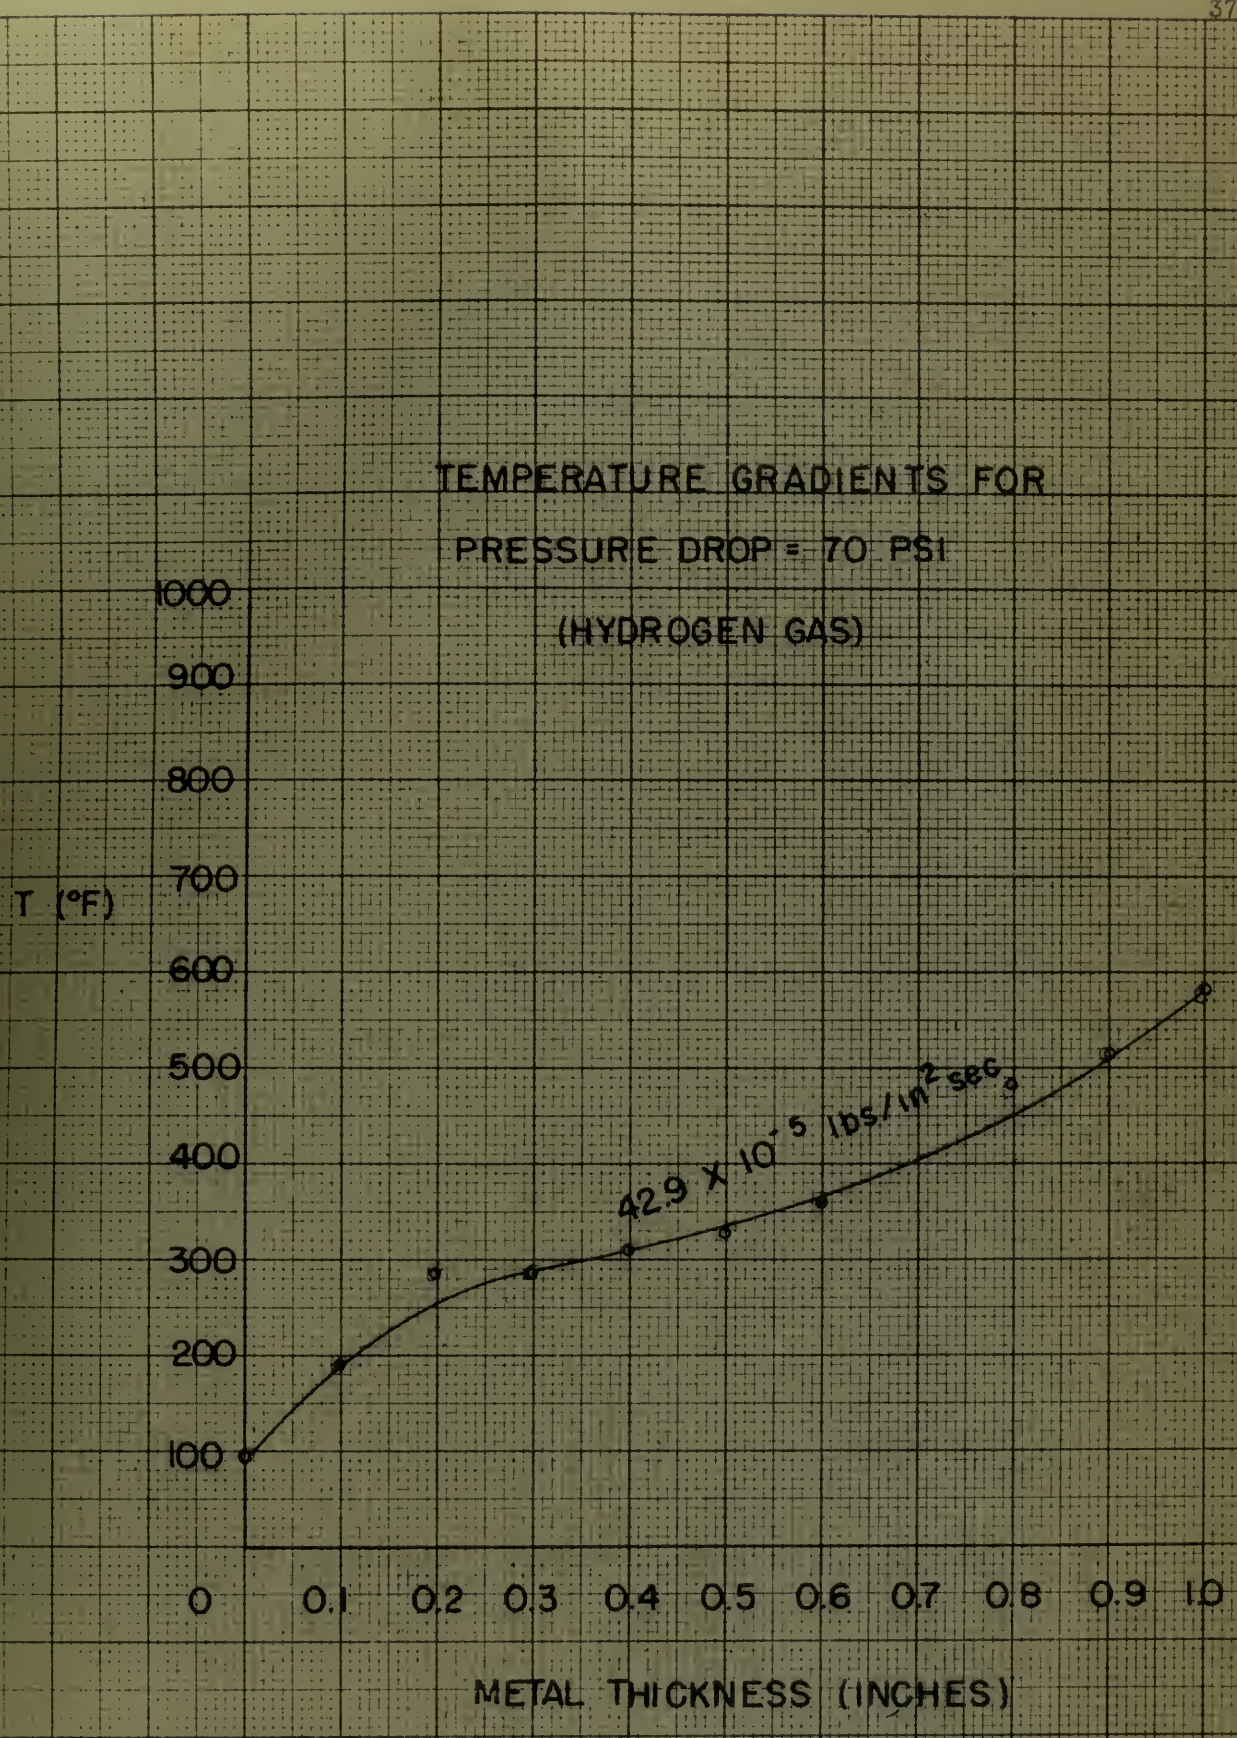
TEMPERATURE GRADIENTS FOR
PRESSURE DROP = 70 PSI
(HYDROGEN GAS)
T (°F)
1000
900
800
700
600
500
400
300
200
100
42.9 X 10⁻⁵ LBS/IN² SEC
0
0.1
0.2
0.3
0.4
0.5
0.6
0.7
0.8
0.9
1.0
METAL THICKNESS (INCHES)

Figure 19

MASS FLOW VS. PRESSURE DROP
CONSTANT FURNACE TEMPERATURES
(NITROGEN GAS)

Figure 20

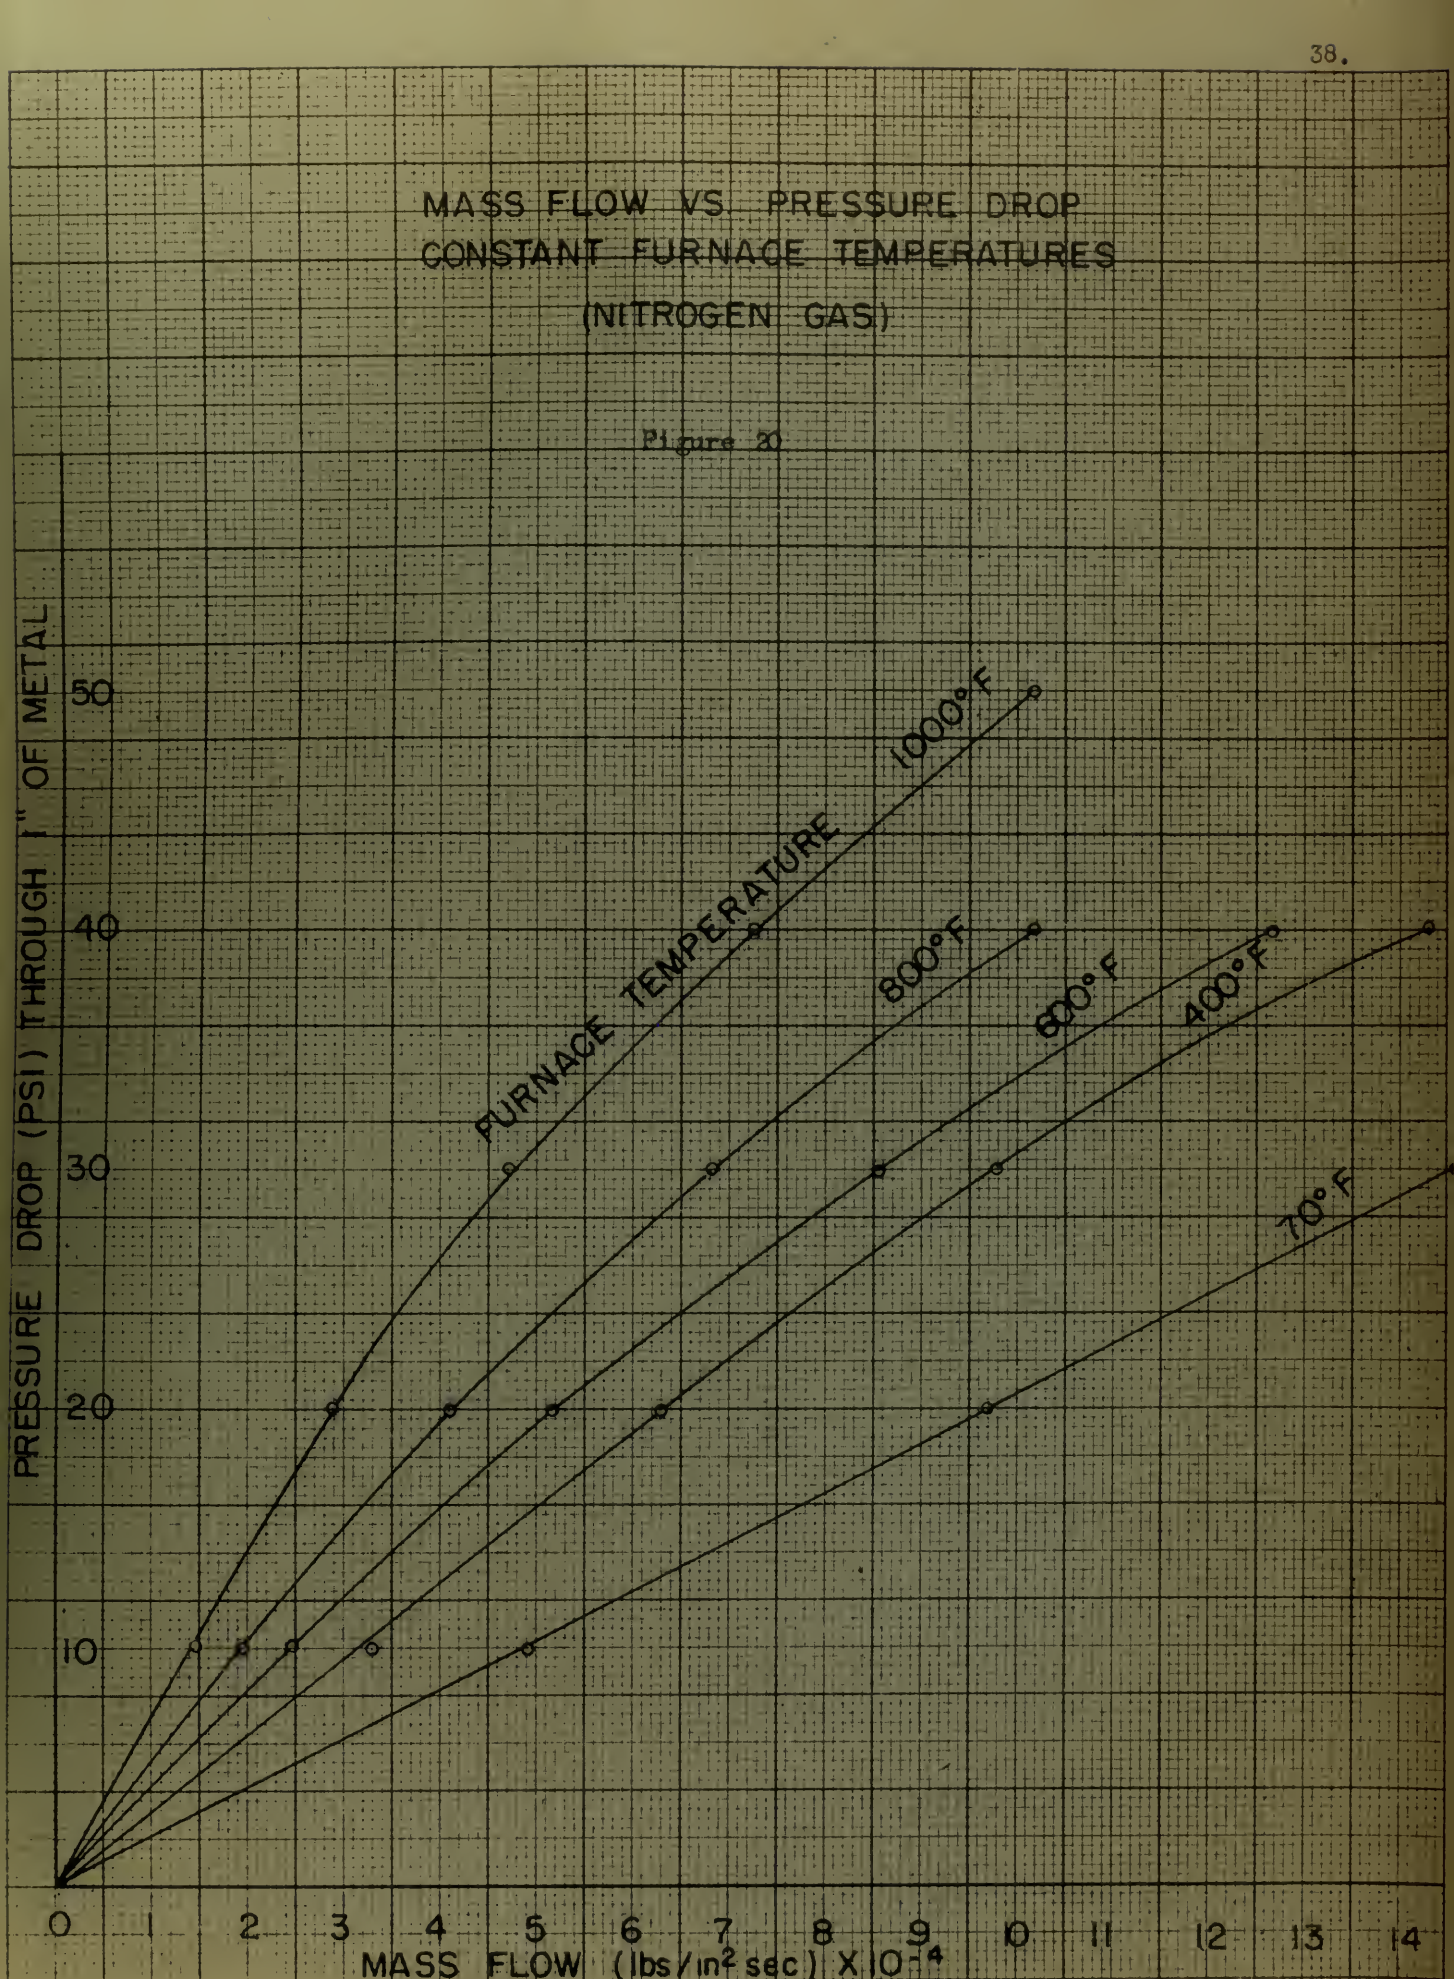

MASS FLOW VS. PRESSURE DROP
CONSTANT FURNACE TEMPERATURES
(HYDROGEN GAS)

Figure 21

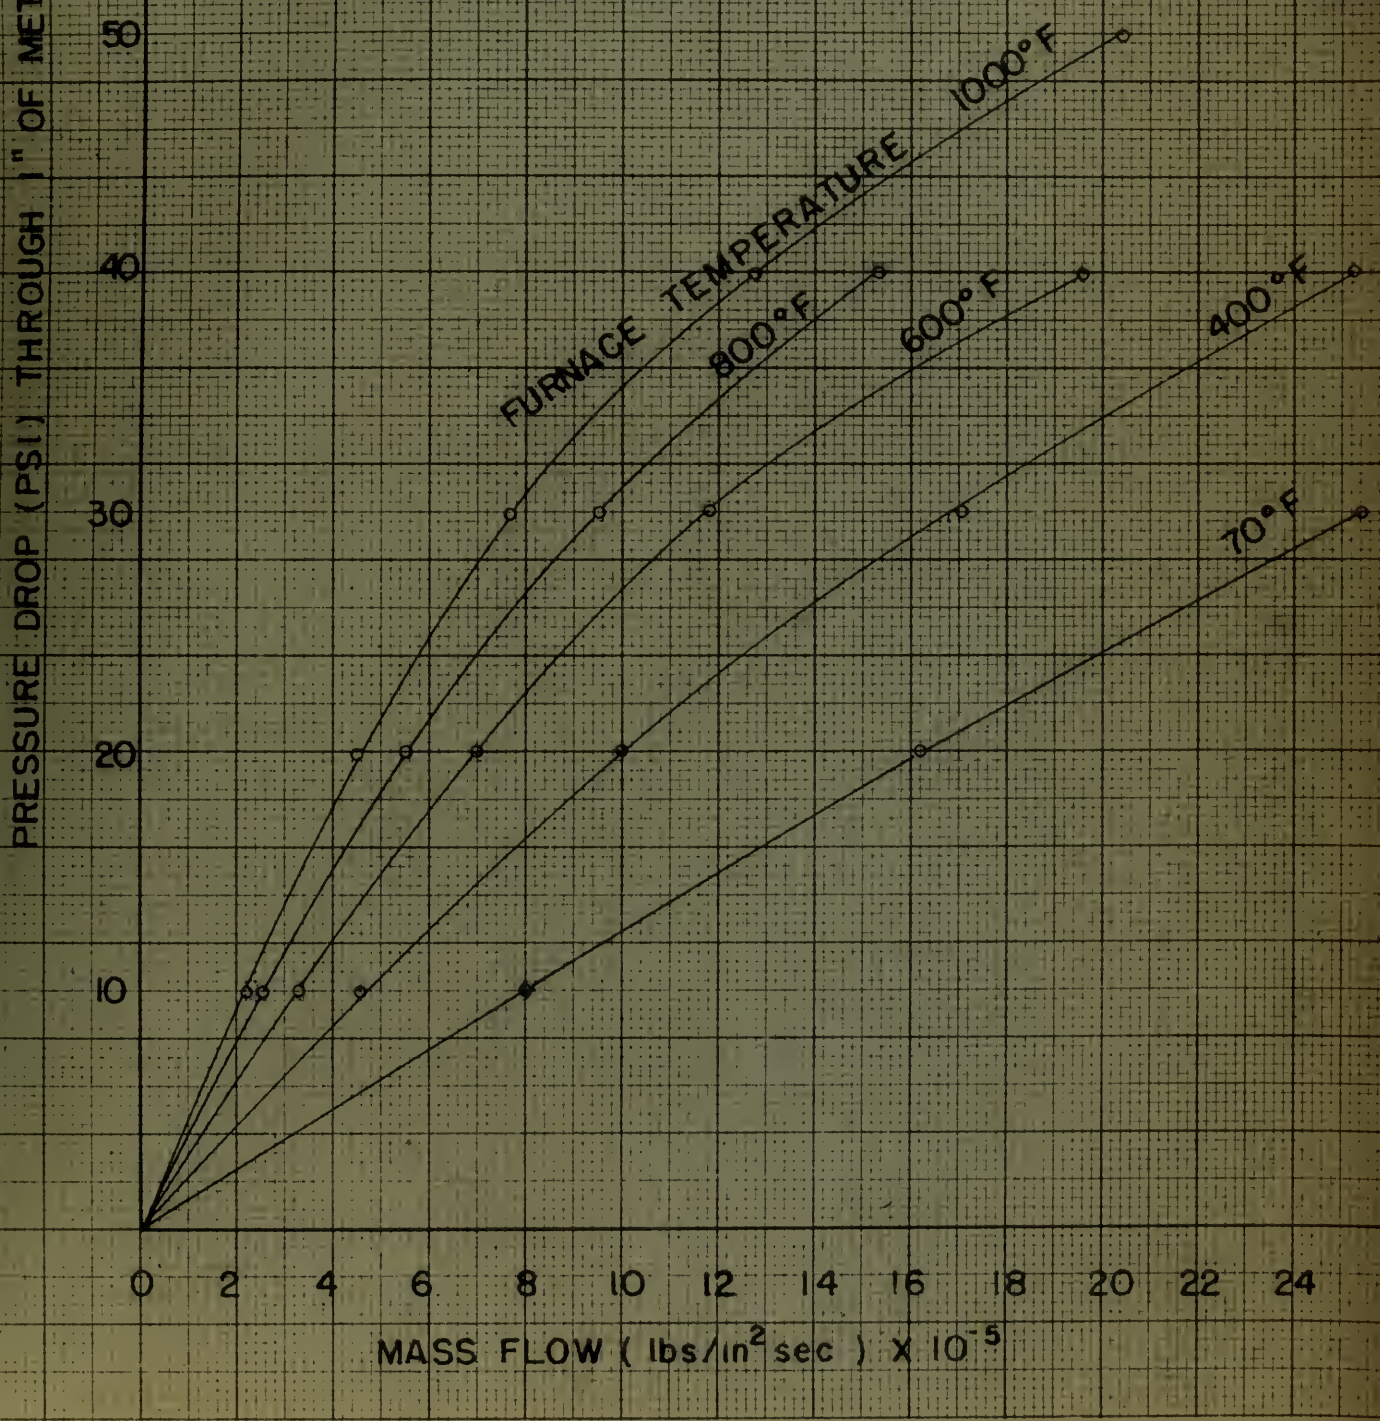

HEAT TRANSFER VS MASS FLOW FOR CONSTANT FURNACE TEMPS.

NITROGEN GAS

Figure 22

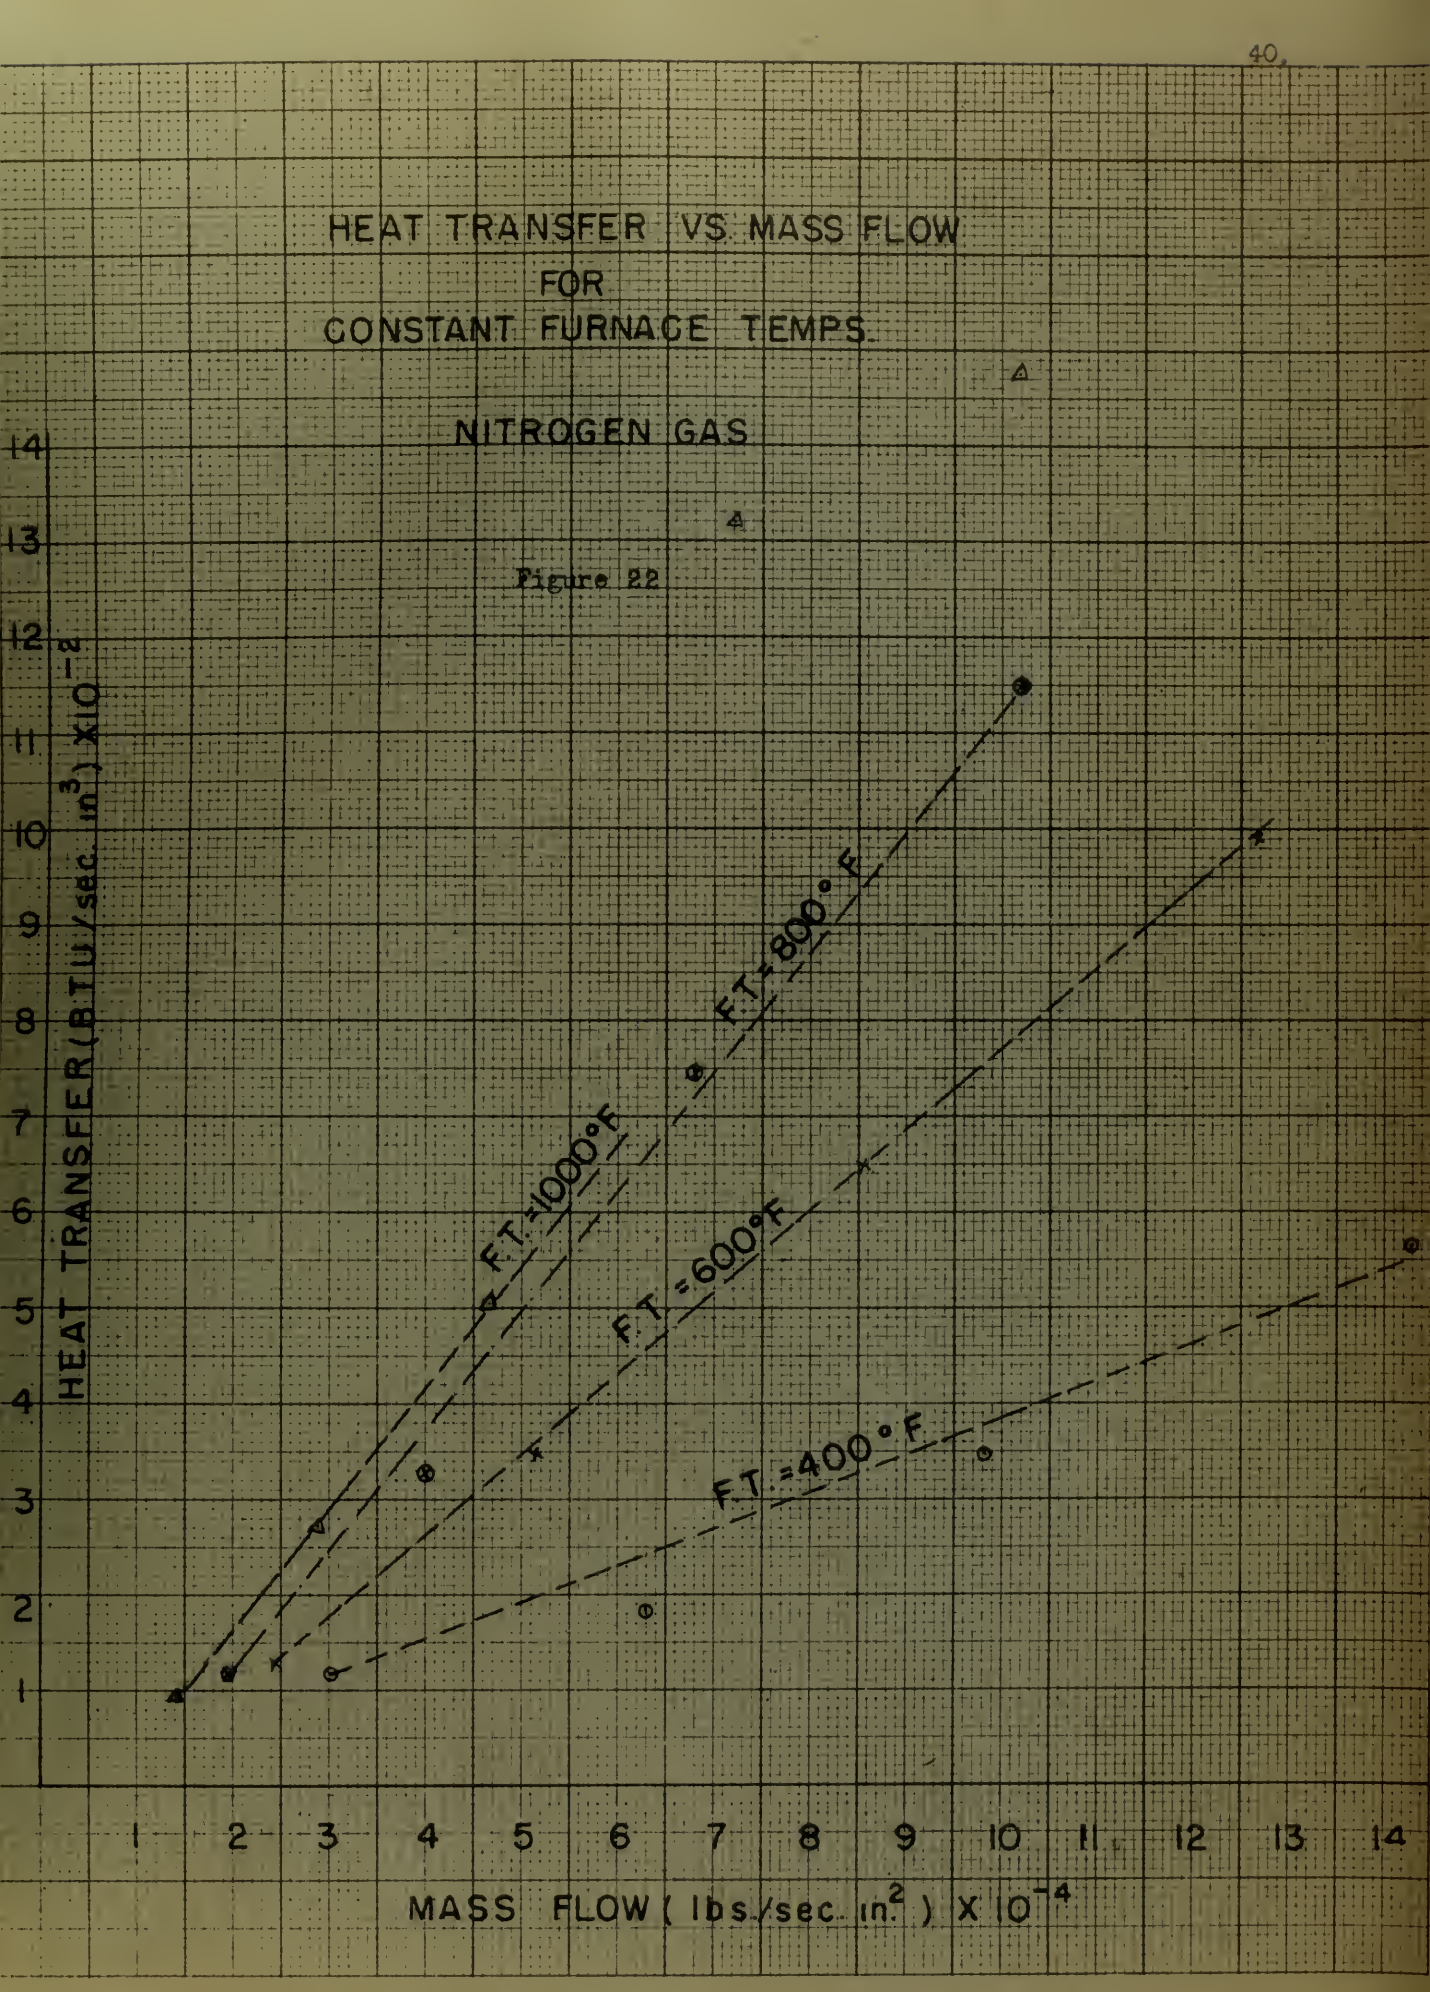

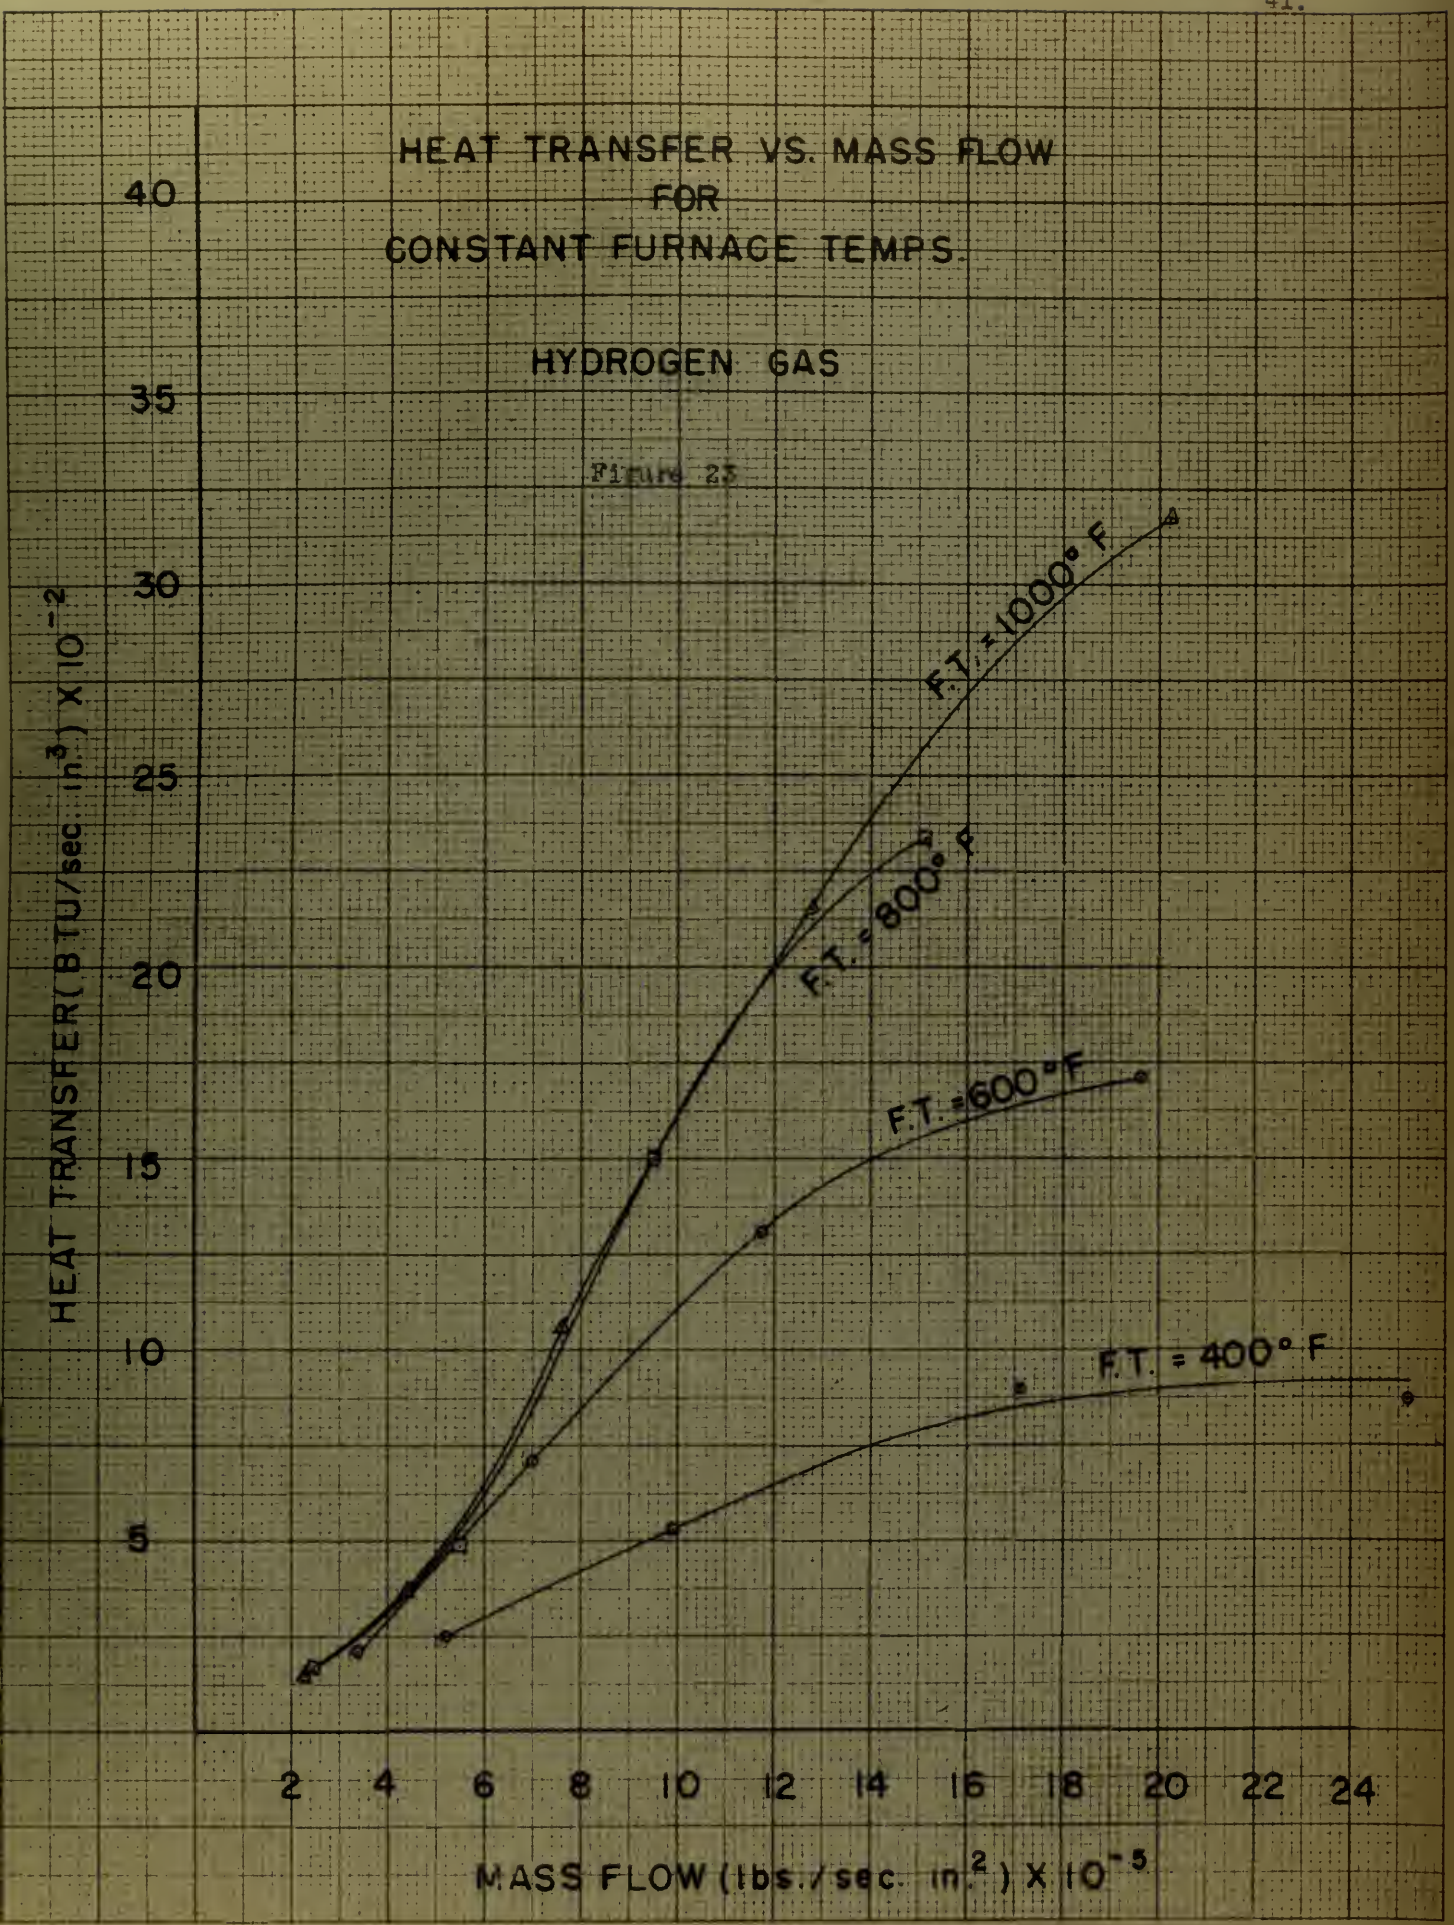
HEAT TRANSFER VS. MASS FLOW
FOR
CONSTANT FURNACE TEMPS.
HYDROGEN GAS
F.T. = 1000° F
F.T. = 800° F
F.T. = 600° F
F.T. = 400° F
HEAT TRANSFER (BTU/sec. in^3) X 10^{-2}
MASS FLOW (lbs./sec. in^2) X 10^{-5}
40
35
30
25
20
15
10
5
2
4
6
8
10
12
14
16
18
20
22
24

Figure 23

CONCLUSIONS

From the results obtained the following conclusions were made:

(1) A cool gas flowing into a heated porous metal very quickly assumes the temperature of the metal.

(2) Heat transfer appears to increase linearly with mass flow up to a certain point above which the results were inconclusive.

(3) The variation of mass flow with pressure drop and temperature change was found to agree with expectations, that is, due to viscosity effects, increasing temperature decreased mass flow and increasing pressure increased mass flow.

(4) External heating is unsatisfactory for obtaining the desired results. It is believed that nearly uniform heating can be achieved by electrical resistance type heating (see Appendix).

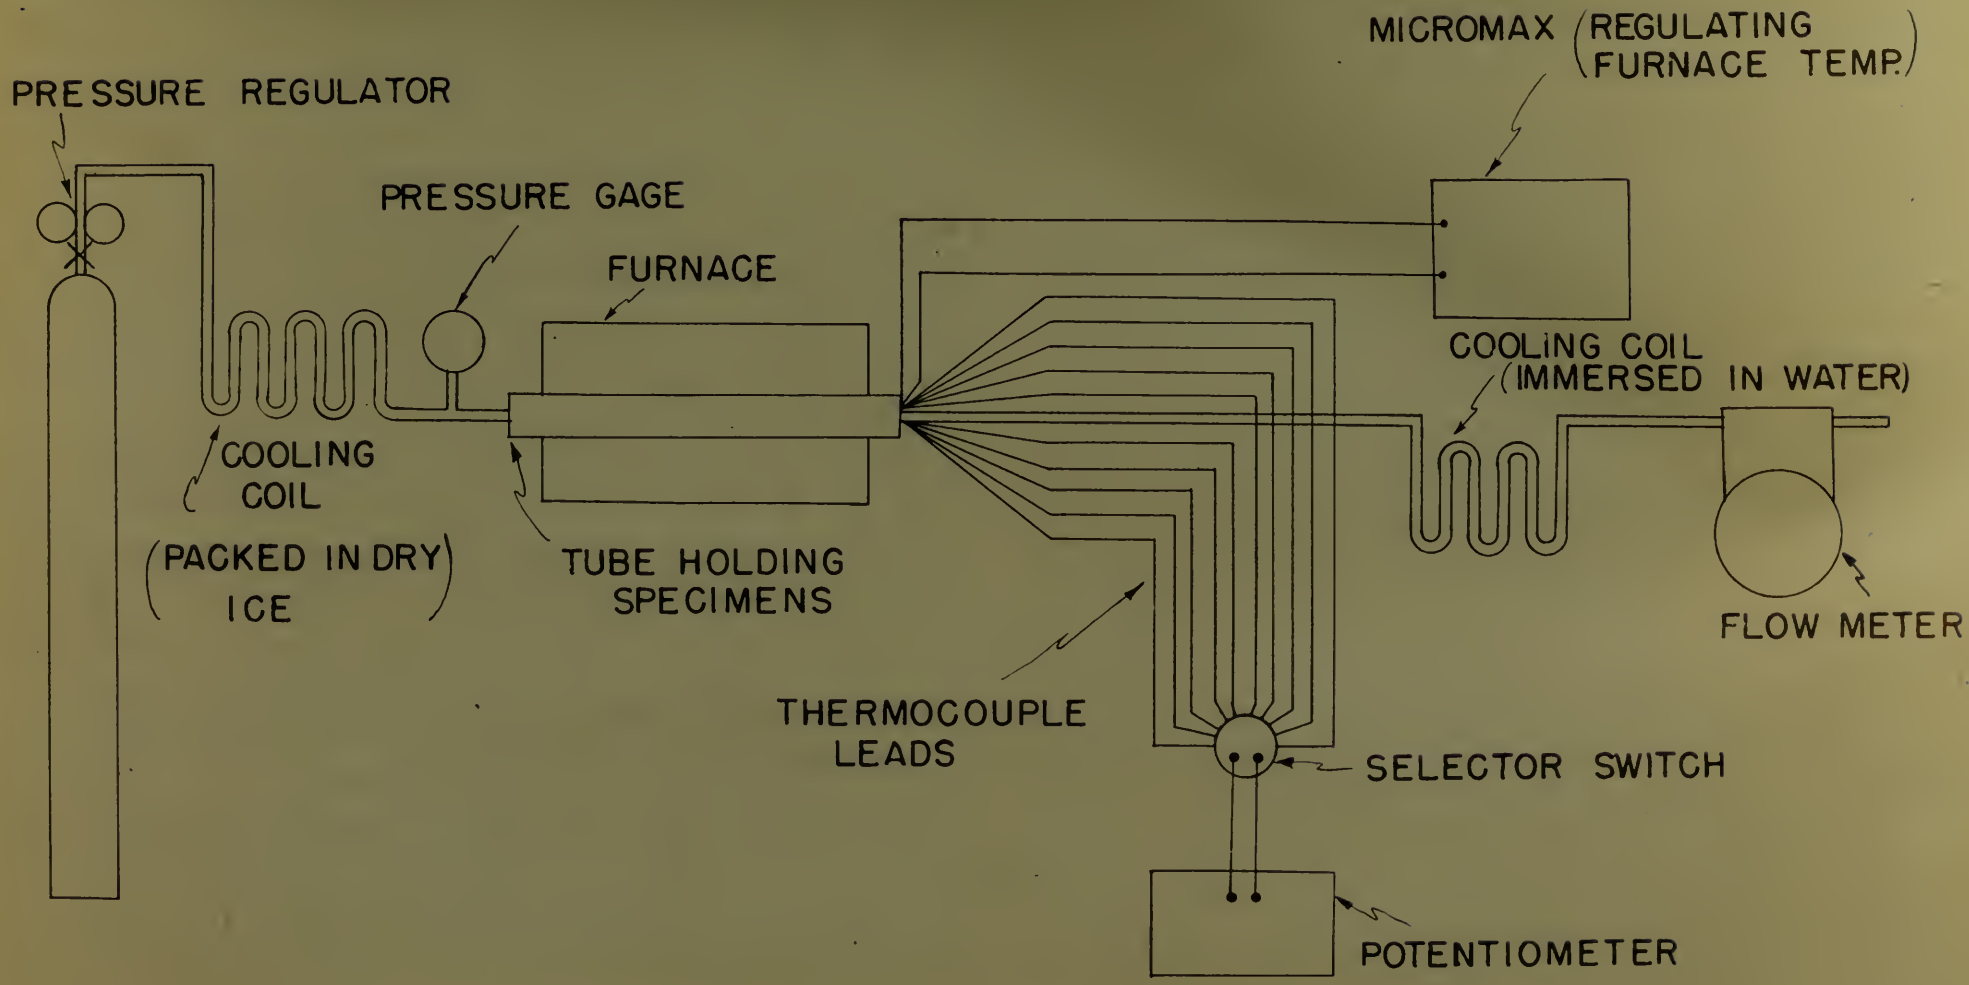

SCHEMATIC DIAGRAM OF APPARATUS

FIG. 24

POROUS METAL PACK
FIG. 25

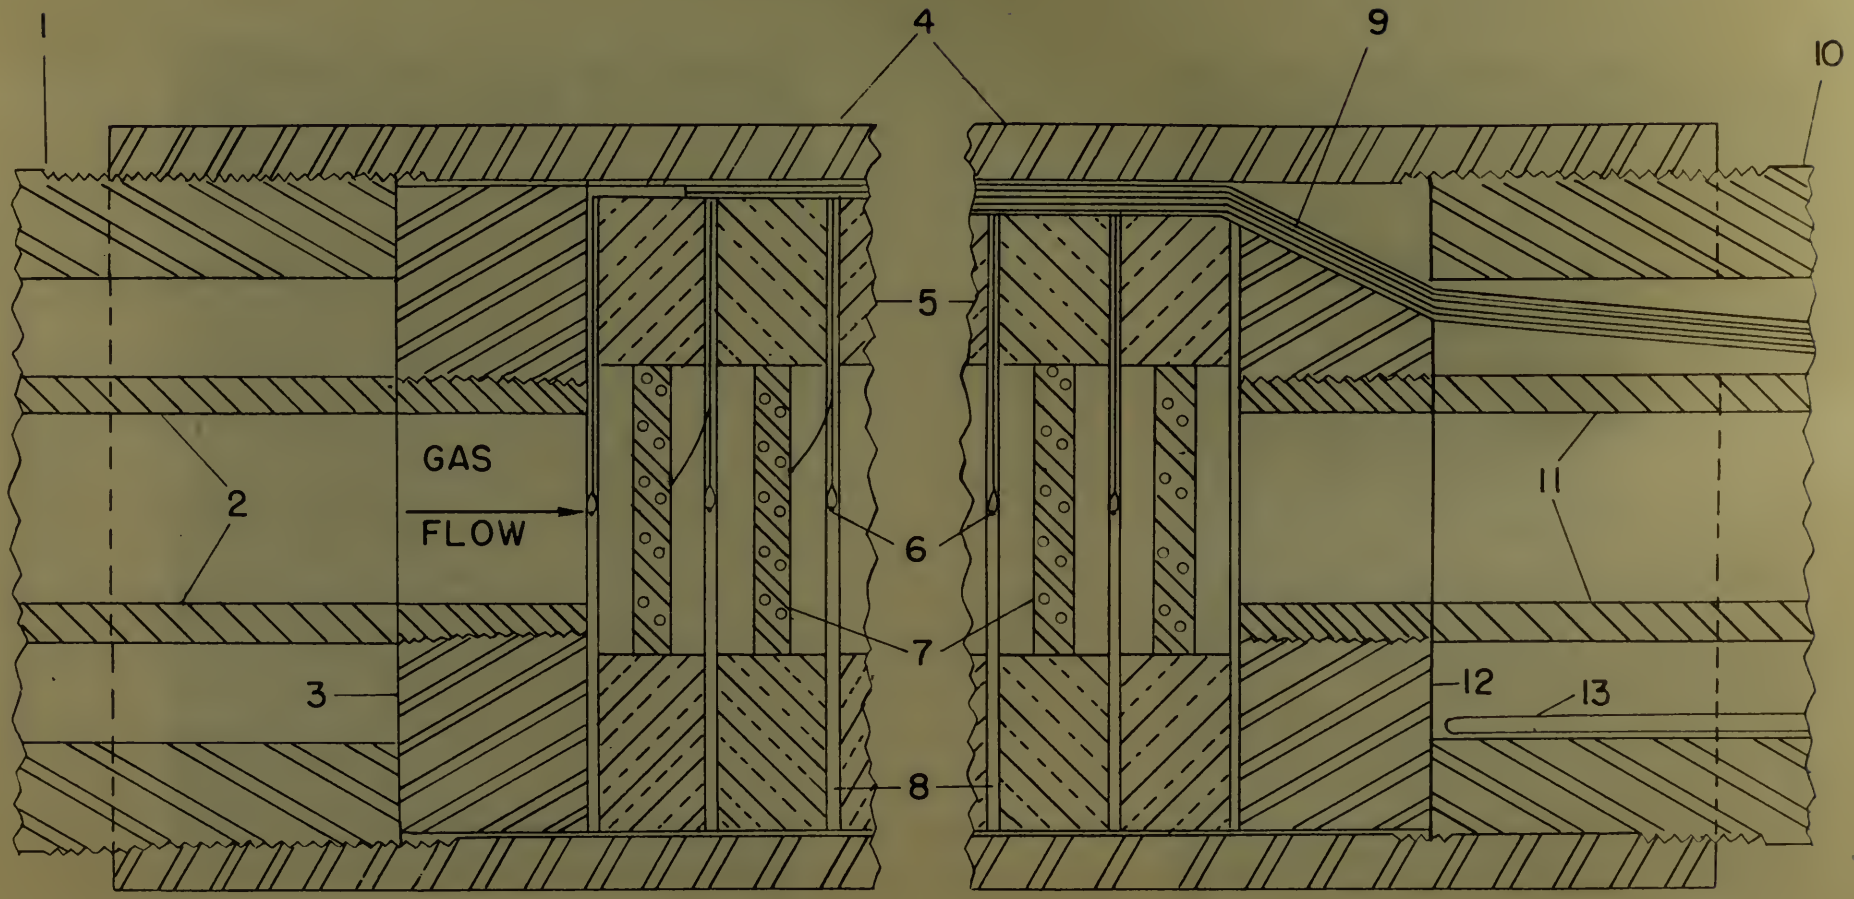

1 – STEEL TUBE
2 – $\frac{3}{8}$" ENTRY PIPE
3 – STEEL DISC
4 – STAINLESS STEEL TUBES
5 – BRASS RINGS
6 – THERMOCOUPLES
7 – POROUS METAL SPECIMENS
8 – GARLOCK GASKETS
9 – THERMOCOUPLE LEADS
10 – STEEL TUBE
11 – $\frac{3}{8}$" DISCHARGE PIPE
12 – STEEL DISC
13 – MICROMAX THERMOCOUPLE

Figure 26
Complete Assembly of Apparatus

Figure 27
Pack Assembly in Open Furnace

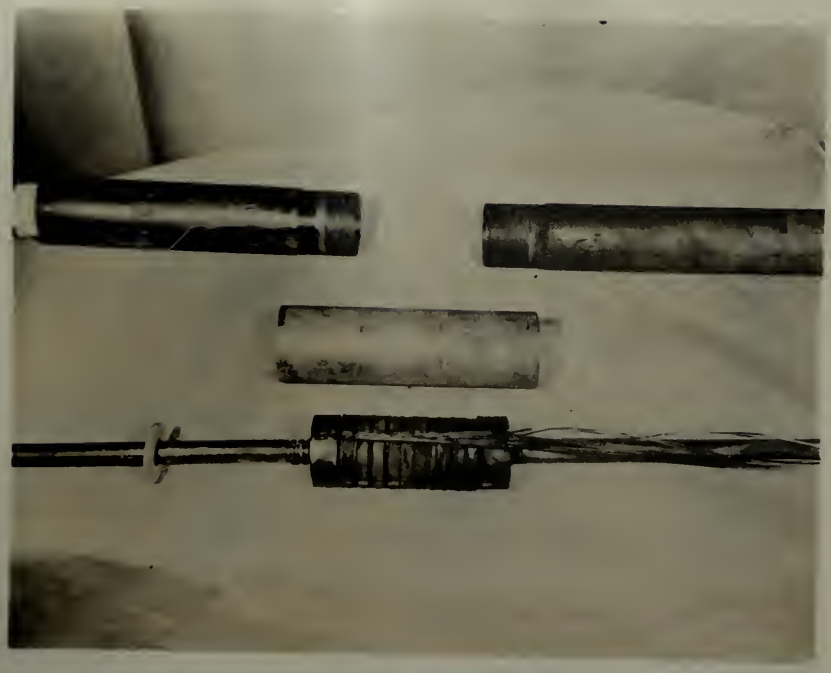

Figure 28
Pack and Containing Tubes

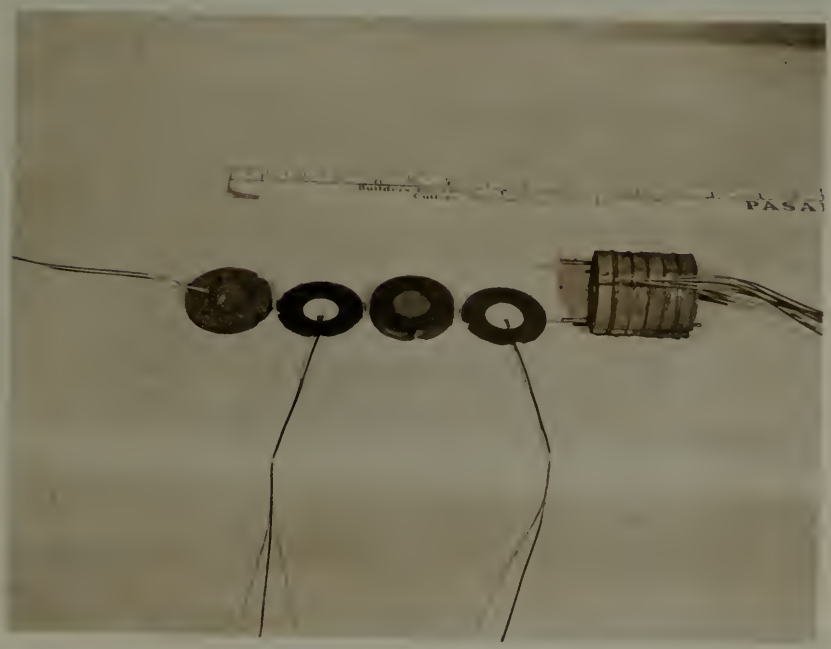

Figure 29
Breakdown of Pack

Figure 30
Assembly of Resistance Heating Apparatus

Figure 31
Breakdown of Resistance Heating Assembly

SAMPLE CALCULATIONS

Symbols:

C_p = Specific Heat (For hydrogen is 3.41 BTU/°F-lb)

Q = Heat transfer per unit volume per unit time (BTU/in^3-sec)

q = Heat transfer per unit time (BTU/sec)

M = Mass flow rate (lbs/sec)

m = Mass flow rate per unit area (lbs/sec-in^2)

p = Pressure (lbs/in^2)

p_o = Atmospheric pressure = 14.7 lbs/in^2)

T = Temperature (degrees Kelvin)

σ = Volumetric flow rate (cu.ft./sec)

ρ = Density of gas (For hydrogen is 0.00562 lbs/ft^3 at standard pressure and temperature)

T_o = Standard temperature = 273° Kelvin

A = Area of cross section (ins.^{3})

t = thickness (in.)

(A) Mass Flow Calculations

Example: Hydrogen Gas

$$\rho = 0.00562 \text{ lbs/ft}^3$$

$$p = 14.7 \text{ lbs/in}^2$$

$$T = 24 + 273 = 297^\circ$$

$$\sigma = \frac{1}{432} \text{ ft}^3/\text{sec}$$

D = 0.75 in.

$$M = \rho \sigma \frac{T_o}{T} \frac{p}{p_o}$$

$$m = \frac{M}{A} = \frac{\rho \sigma}{A} \frac{T_o}{T} \frac{p}{p_o}$$

$$A = \frac{\pi}{4} (0.75)^2 = 0.4415 \text{ in}^2$$

$$m = \frac{(0.00062)(273)(14.7)}{(462)(.4415)(2.7)(14.7)}$$

$$m = 2.33 \times 10^{-5} \text{ lbs/sec-in}^2$$

(8) Heat Transfer Calculations:

Calculations for the heat transfer curves plotted in Figs. 22 and 23 were based upon the heat transferred by the fifth specimen numbered from the inlet end.

$$q = WC_p (T_2 - T_1)$$

$$q = q/Ac = \frac{m C_p (T_2 - T_1)}{t}$$

Example:

Hydrogen gas

$m = 7.80 \times 10^{-5}$ lbs/in^2-sec

$C_p = 3.81$ BTU/lb - $^\circ$F

$T_2 = 820^\circ$F

$T_1 = 730^\circ$F

$t = 0.1$ inches

$$q = \frac{(7.80)(3.81)(820-730) \times 10^{-5}}{0.1}$$

$q = 10.32 \times 10^{-2}$ BTU/in^3-sec

Discussion of Efforts to Accomplish Uniform Heating of a Specimen by Electrical Resistance Heating

It was determined that the greatest shortcoming of the apparatus used to make the subject study was the external heating, which departed considerably from the desired uniform heating.

Subsequent to most of the preparation of this report an effort was made to accomplish uniform heating by electrical resistance heating. A 47% porous specimen containing 20% iron and 80% nickel was prepared in a modified dumbell shape (Fig. 31). The center section was solid and cylindrical, 1/2 inches in diameter and 4 inches long. The ends were solid and cylindrical 3/4 inches in diameter and each 1 inch long. In order to pass gas axially through the specimen, copper tubing was fitted over and silver soldered to the ends of the specimen. A flanged joint (Fig. 32) was placed in each copper tube to permit the introduction of thermocouples into the incoming and outgoing gas streams. The large specimen ends were connected to the terminals of a variable power source having 100 kva maximum available power. The gas was lead in and out through saran tubing to provide electrical insulation. Approximately 8 kva applied at 25 volts and 320 amperes was found to be adequate to heat the center section of the specimen to a bright cherry red. It was readily seen that while a gain had been made in the efforts to accomplish uniform heating across the center section, the large ends and the heavy copper terminals were drawing heat out of the ends of

the center section causing this to be at a relatively low temperature compared to the cherry red center. Rolling, polishing, and chromium plating were each tried in separate attempts to make the specimen's surface gas tight. Each was found to be inadequate to prevent the escape of gas radially. These complications led to discarding the set-up as a means for making quantitative observations. Therefore, no numerical data were recorded from the observations of this equipment.

It is believed that both of the before mentioned shortcomings of this apparatus can be minimized or eliminated by the use of a hollow cylinder. In this set-up a hollow cylinder would be heated by electrical resistance heating while a gas introduced from the open ends is flowed radially outward and sampled to determine temperatures. The problem of sealing the specimen surface would be eliminated. It is believed that if the tube is made long relative to its metal cross sectional area the flow of heat into the ends and power terminals would be minimized and a reasonable degree of uniform heating would be accomplished. By using a thickness which was small compared to the length of the solid dumbell specimen, described above, a relatively large mass flow could be realized.

DATE DUE

DUDLEY KNOX LIBRARY
NAVAL POSTGRADUATE SCHOOL
MONTEREY CA 93943-5101

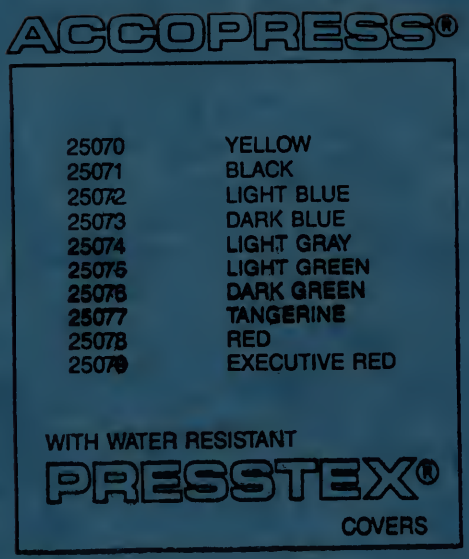

GAYLORD S

3 2768 00018999 7

ACCO. USA
WHEELING, ILLINOIS 60090
ITEM NO. 25072
0 50505 25072 1
LT. BLUE/BLEU/AZUL CLARO
MADE IN USA